

**Inverse order-disorder transition of charge stripes**

Shu-Han Lee, Yen-Chung Lai, and Chao-Hung Du\*

*Department of Physics, Tamkang University, Tamsui District, New Taipei City 25137, Taiwan*

Alexander F. Siegenfeld

*Department of Physics, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, Massachusetts 02139-4307, USA*

Ying-Jer Kao†

*Advanced Center for Theoretical Science and Department of Physics, National Taiwan University, No. 1, Sec. 4, Roosevelt Rd. Taipei 10607, Taiwan*

Peter D. Hatton

*Department of Physics, Durham University, Durham DH1 3LE, United Kingdom*

D. Prabhakaran

*Department of Physics, University of Oxford, Clarendon Laboratory, Parks Road, Oxford OX1 3PU, United Kingdom*

Yixi Su

*Juelich Centre for Neutron Science JCNS, Forschungszentrum Juelich GmbH, Outstation at MLZ, Garching D-85747, Germany*

Di-Jing Huang

*National Synchrotron Radiation Research Center, 101 Hsin-Ann Road, Hsinchu 30076, Taiwan*

(Received 9 February 2015; published 9 November 2015)

We report an unusual transition behavior of charge stripes in  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  using x-ray scattering. The segregated holes in  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  are observed to form anisotropic stripes in the  $a \times b$  plane of the crystal space below the transition temperature  $T \simeq 238$  K, and at the same time, display an unusual inverse order-disorder transition along the  $c$  axis. Using a phenomenological Landau theory, we show that this inverse transition is due to the interlayer coupling between the charge and spin orders. This discovery points to the importance of the interlayer correlations in the strongly correlated electrons system.

DOI: [10.1103/PhysRevB.92.205114](https://doi.org/10.1103/PhysRevB.92.205114)

PACS number(s): 71.27.+a, 71.30.+h, 71.45.Lr

Doped Mott insulators have served as a rich playground for strongly correlated electron systems, yet the physics is still not fully comprehended. The complexity results from the interplay between competing orders, such as charge, spin, orbital, and lattice, and the strong quantum fluctuations [1]. In the model system of high- $T_c$  superconductor  $\text{La}_2\text{CuO}_4$ , substitution of La with Sr or Ba induces segregated holes that form unidirectional self-organized electronic stripes in the  $a \times b$  plane of the crystal space [2]. Experimentally, such a phenomenon has been observed in neutron, x-ray, and electron diffractions, and it is shown that transport behavior depends strongly on the hole concentration [3,4]. These ordered electronic phases are understood to arise due to the Coulomb-frustrated separation of electronic domains at the nanoscale [5,6]. In these phases, there exist locally Mott insulating regions with magnetic (spin) order, separated by more metallic regions with higher concentrations of doped holes. Taking the in-plane fluctuations into consideration, these ordered charges could form the exotic electronic liquid-crystal phases [7,8]. This intralayer coupling between the ordered charges and spins has been widely discussed and observed in Cu- and Fe-based

superconductors [9–12]. It is natural to ask what role the interlayer coupling between the charge and spin orders in different planes plays in these systems [13,14].

Using x-ray scattering measurements on single-crystal samples of  $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$  (LSNO), we report an unusual inverse order-disorder transition due to the interlayer coupling of the in-plane charges and spins. It is well established that there can exist both smectic and striped-liquid phases of in-plane charge and spin ordering in LSNO [15–18]. LSNO has a tetragonal structure [Fig. 1(a)], and is isostructural with the superconducting cuprate LSCO. Both LSNO and LSCO are antiferromagnetic (AFM) Mott insulators in the absence of hole doping. While LSCO becomes a high- $T_c$  superconductor for small amounts of hole doping, LSNO remains insulating for doping levels of up to 90% [19].

In LSNO the doped holes condense, leaving, within each two-dimensional (2D) NiO layer, an alternating pattern of AFM domains (spin stripes) separated by charge stripes [Fig. 1(b)]. In the reciprocal space of the tetragonal crystal structure ( $F4/mmm$ ), the stripes lead to charge and spin satellite reflections with wave vectors of  $\mathbf{Q}_{\text{CO}} = (H \pm 2\epsilon 0 L_1)$  and  $\mathbf{Q}_{\text{SO}} = (H \pm \epsilon 0 L_2)$ , where  $H$  and  $L_2$  are integers,  $L_1$  is odd, and  $\epsilon$  is determined by hole concentration with  $\epsilon \sim x$ . For  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  ( $x = 1/3$ ), the charge and spin orders are commensurate with the lattice, and satellite reflections from the charge stripes superimpose on those from the spin stripes

\*chd@mail.tku.edu.tw

†yjkao@phys.ntu.edu.tw

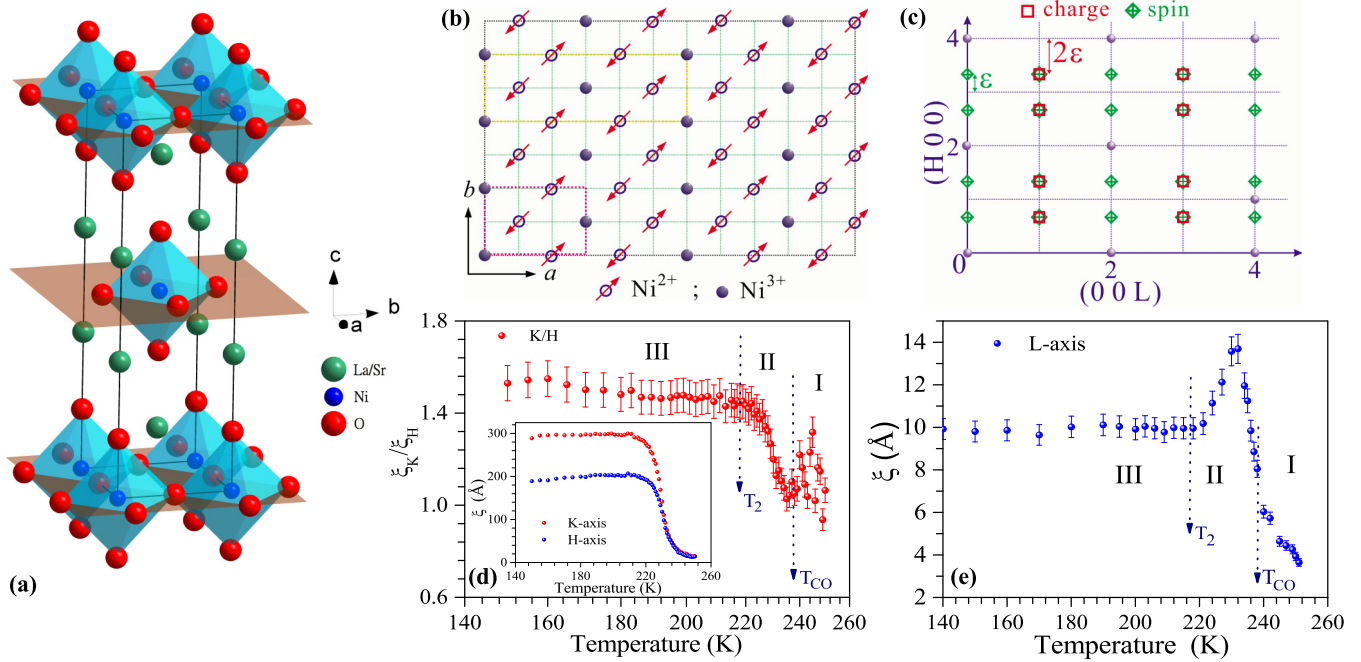


FIG. 1. (Color online) Schematic views of crystal structure and charge stripes, and the evolution of correlation lengths of charge stripes as a function of temperature. (a) The crystal structure of  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$ . (b) Schematic view of charge and spin stripes in  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  in  $\text{NiO}_2$  planes of the tetragonal unit cell. The arrows represent the  $\text{Ni}^{2+}$  ions, and solid circles are the holes. Yellow and red boxes indicate the size of the spin and charge modulations. (c) The satellite reflections of charge and spin stripes in the  $(H\ 0\ L)$  plane of reciprocal space. Since the incommensurability  $\epsilon \sim 0.33$ , charge reflection satellites superimpose on spin reflections. (d) Temperature evolution of the ratio of the correlation lengths along the  $K$  and  $H$  directions. The data can be divided into three regions with two transition temperatures of  $T_{CO}$  ( $\sim 238\text{K}$ ) and  $T_2$  ( $\sim 218\text{K}$ ), as marked I, II, and III. The inset shows the evolution of the correlation lengths of the charge stripes along the  $H$  and  $K$  directions as a function of temperature. (e) Evolution of the correlation length along the  $L$  direction as a function of temperature. As can be seen, there is an inverse order-disorder transition at around 230 K. The correlation lengths were extracted from the inverse of FWHM (full width at half maximum) of the charge-ordering reflections.

[Fig. 1(c)], a condition that proves essential for the inverse transition of the interlayer charge order.

For this study, high-quality single crystals of  $\text{La}_{1-x}\text{Sr}_x\text{NiO}_4$ ,  $x = 0.225, 0.33$ , and  $0.4$ , were grown by the floating zone method at University of Oxford. The crystals were characterized and orientated using conductivity measurements and an in-house x-ray diffractometer, and the surface was polished using  $0.1\ \mu$  diamond paste. The values of  $x$  were further confirmed by checking the transition temperatures of charge modulation using synchrotron x-ray scattering. Synchrotron x-ray scattering experiments were performed on the beam lines BL07 and SP12B1 of NSRRC (Taiwan) and SP8 (Japan). The incident x-ray energy was selected to be 10 keV. The sample was mounted on a closed-cycle cryostat on a multicircle diffractometer. A single crystal of LiF  $(0\ 0\ 1)$  was used as an analyzer to define the scattered x rays from the sample. The experimental resolution function was determined to be  $\epsilon_H^{-1} \sim 0.0019\ \text{\AA}^{-1}$ ,  $\epsilon_K^{-1} \sim 0.001\ \text{\AA}^{-1}$ , and  $\epsilon_L^{-1} \sim 0.015\ \text{\AA}^{-1}$  as measured on the Bragg peak  $(4\ 0\ 0)$  near the charge-ordering peaks at  $T = 140\ \text{K}$ , with the sample mosaic width  $\sim 0.02^\circ$ . For the study of spin stripes, resonant soft x-ray scattering measurements were performed on the beam line BL05B3 of NSRRC. The measurements were performed to scan the spin-stripe reflection  $(0.66\ 0\ 0)$  through the  $L_3$  edge of Ni.

Figure 1(d) shows, as a function of temperature, the ratio of the charge correlation lengths along the  $H$  and  $K$  directions in the reciprocal space. The data can be divided into three regions with two transition temperatures of  $T_{CO}$  ( $\sim 238\text{K}$ ) and  $T_2$  ( $\sim 218\text{K}$ ), as marked I, II, and III. In regime I ( $T > 238\text{K}$ ), the segregated charges are in an disordered and isotropic state. Upon cooling, the segregated charges form anisotropic charge stripes, and the anisotropy displays a temperature-dependent behavior in regime II ( $218\ \text{K} < T < 238\ \text{K}$ ). Finally, the anisotropy reaches nearly constant in regime III (below  $T_2$ ). The detailed peak profiles can be seen in Figs. 5 and 6 of the Appendix A. LSNO has been known not to have any lattice distortions at low temperatures [20,21], so this anisotropic behavior is a result of an intrinsic charge modulation.

The unusual data comes from the measurements taken along the  $L$  direction in the reciprocal space, shown in Fig. 1(e). Cooling from high temperatures, the charge correlation starts to build up significantly along the  $c$  axis of the crystal at around  $T = 238\ \text{K}$ , and the charge correlation lengths start to increase from  $\xi = \sim 6\ \text{\AA}$  to  $14\ \text{\AA}$  as temperature is cooled down to  $T = 230\ \text{K}$ . At this temperature, the interlayer charge correlation spans over two  $\text{NiO}$  layers and it seems that a full 3D ordering will eventually develop if there is no existence of any imperfections in the crystal [22]. However, when the temperature is further decreased, the interlayer

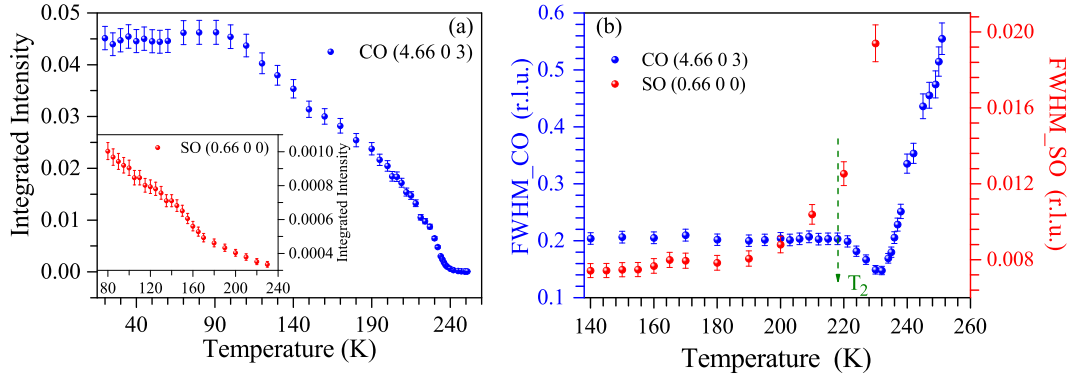


FIG. 2. (Color online) Interplay between charge and spin stripes. (a) Temperature dependence of the integrated intensity for charge ordering reflection (CO) and spin ordering reflection (SO). (b) Evolution of peak width as a function of temperature for the CO reflection (4.66 0 3) (blue dots) and the SO reflection (0.66 0 0) (red dots). The charge reflection was measured along the  $L$  direction using hard x rays, and the spin reflection was measured along the  $H$  direction by resonant soft x-ray diffraction. It can be seen that the spin-stripe order exists up to  $\sim 230$  K. The onset of the interlayer correlation suppression coincides with the onset of the in-plane spin order, indicating a close relationship between the two.

charge correlation starts to decrease, rather than increase, and the inverse order-disorder transition occurs. Finally, the interlayer charge correlation length reaches  $\xi = \sim 10$  Å below  $T = 218$  K, where both the charge and spin stripes are well established. We realize, for the  $c$ -axis correlation length at low temperatures, that there exists a discrepancy between the current data and the reported result [22]. This difference could be due to the different sample treatments as those reported by Hücker *et al.* [21]. Attention was also paid to study the thermal effect of charge stripes. Under different thermal sequences, (as described in Appendix B), charge stripes show a thermal hysteresis behavior around the transition (see Appendix B, Fig. 8), suggesting that charge stripes are in a nonequilibrium state just below the transition temperature.

Experiments were also conducted to measure the spin stripes using resonant soft x-ray diffraction. Figure 2(a) shows the temperature dependence of the integrates intensity of the charge-stripe reflection (4.66 0 3) and spin-stripe reflection (0.66 0 0). This evidences that charge stripes undergo a second-order phase transition. This is consistent with our previous report of a quenched disordered charge stripes [22]. According to our model, this quenched disordered state is the consequence of the interplay between charges and spins. It is worth noting that the very weak spin ordering reflection is still observable at temperature of 230 K by means of resonant soft x-ray diffraction at the Ni  $L_3$  edge. This behavior is in accord with the reported result by Anissimova *et al.* using neutron scattering, and suggesting a strong coupling between the charge and spin stripes [17]. Figure 2(b) shows the temperature evolution of the peak profile of a spin-stripe satellite reflection at (0.66 0 0) measured along the  $H$  direction, which serves as a measure of in-plane spin order, and of a charge-stripe satellite reflection at (4.66 0 3) along the  $L$  direction, which serves as a measure of interlayer charge correlation. Although the spin-stripe transition occurs at a temperature of around 190 K, the satellite reflection persists up to temperatures as high as 230 K, indicating a dynamic spin fluctuations at high temperatures [17,18]. The onset of the interlayer charge-order suppression coincides with the appearance of the in-plane spin-stripe order, suggesting that the in-plane spin-stripe order

plays an important role in the inverse transition of the interlayer charge order.

In order to model the observed behavior in LSNO, we construct a Landau theory for the spin and charge-stripe orders for a bilayer system with 2D layers. For simplicity we assume that the spin and charge order in each layer can be described by single complex Fourier coefficients and that the spin order is collinear; thus the order parameters can be written as  $\mathbf{S}_i = |S_i| e^{i(\phi_i + \mathbf{r}_i \cdot \mathbf{q}_i^S)} \hat{\mathbf{m}}_i$  and  $\rho_i = |\rho_i| e^{i(\theta_i + \mathbf{r}_i \cdot \mathbf{q}_i^\rho)}$ , where  $\mathbf{q}_i^S$  is measured relative to the in-plane antiferromagnetic ordering vector  $\mathbf{Q} = (1, 0, 0)$  and  $i \in \{1, 2\}$  denotes the layer index. We take  $2\mathbf{q}_1^S = 2\mathbf{q}_2^S = \mathbf{q}_1^\rho = \mathbf{q}_2^\rho$ , so as to allow coupling between the order parameters within and between layers [23].

Starting from the most general Landau free energy for a single layer that includes all symmetry allowed terms up to the fourth order and then applying a few simplifications yields [23]

$$F_i = \frac{1}{2} r_s |S_i|^2 + |S_i|^4 + \frac{1}{2} r_\rho |\rho_i|^2 + |\rho_i|^4 + \lambda_1 |S_i|^2 |\rho_i| \cos(2\phi_i - \theta_i). \quad (1)$$

We take the free energy due to the interlayer coupling to be

$$F_c = \lambda_\rho (\rho_1 \rho_2^* + \text{c.c.}) + \lambda_2 [(\mathbf{S}_1 \cdot \mathbf{S}_1) \rho_2^* + (\mathbf{S}_2 \cdot \mathbf{S}_2) \rho_1^*] + \text{c.c.} \\ = 2\lambda_\rho |\rho_1| |\rho_2| \cos(\theta_1 - \theta_2) + 2\lambda_2 [ |S_2|^2 |\rho_1| \cos(2\phi_2 - \theta_1) \\ + |S_1|^2 |\rho_2| \cos(2\phi_1 - \theta_2) ], \quad (2)$$

where the  $\lambda_\rho$  term is due to Coulomb repulsion between layers and the  $\lambda_2$  term is due to the fact that the holes are to some extent delocalized between layers.

The total free energy is  $F = F_1 + F_2 + F_c$ , but considering that intralayer interactions are far stronger than interlayer ones, the approximate values of  $|S_i|$ ,  $|\rho_i|$ , and  $2\phi_i - \theta_i$  can be determined by examining only the single-layer free energy, resulting in  $|S_1| = |S_2| \equiv S$  and  $|\rho_1| = |\rho_2| \equiv \rho$ , and leaving only the interlayer phase shift of  $\alpha \equiv \theta_1 - \theta_2$  to be determined by the interlayer coupling. Minimizing the intralayer free energies requires  $\cos(2\phi_i - \theta_i) = -1$ , since  $\lambda_1$  is positive [23], and so we obtain  $F_c = 2\rho(\lambda_\rho \rho - 2\lambda_2 S^2) \cos \alpha$ . A good measure of the strength of the interlayer coupling is the stiffness of the phase shift  $C \equiv \frac{\partial^2 F_c}{\partial \alpha^2} = |2\rho(\lambda_\rho \rho - 2\lambda_2 S^2)|$  at

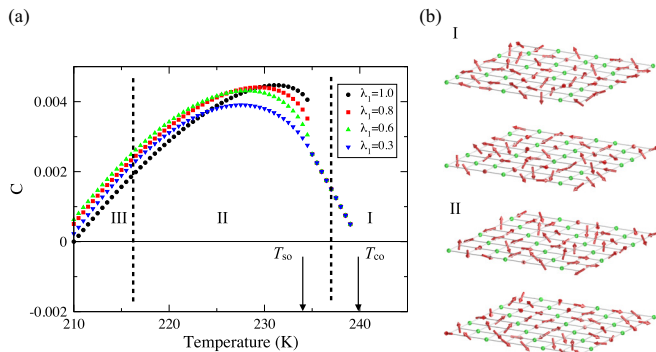


FIG. 3. (Color online) Bilayer correlations from the Landau theory, and spin and charge configurations in different phases. (a) Plot of  $C$ , the stiffness of the interlayer phase shift defined in the text, as a function of temperature for several intralayer charge-spin coupling constants. (b) Real-space configurations of the states in different temperature regimes. In the high-temperature regime I, there exists no or very weak in-plane charge order and the correlation between layers is small. In regime II, charge stripe order develops while the spins remain disordered. The charge stripes between layers tend to be anti-phase to minimize the Coulomb repulsion between layers.

equilibrium. For a large  $C$ , the phase shift between layers of the charge stripes is harder to fluctuate and the phase angles tend to be antiphase to minimize the free energy. On the other hand, for small  $C$ , the phase shift between layers becomes less rigid and allows for more fluctuations, leading to a reduction of interlayer correlation. It is now clear why the interlayer correlations at first increase and then decrease as the temperature  $T$  is lowered: at high temperatures,  $\rho = S = 0$  so there are no interlayer correlations. Charge order appears first and so  $C$  at first increases, but at lower temperatures spin order also appears thus causing  $C$  to then decrease. At still lower temperatures we expect the Landau theory to no longer accurately model the system.

Giving  $r_\rho$  and  $r_s$  linear temperature dependence and taking  $\lambda_1$  to be temperature independent,  $C$  will always, after an initial increase, decrease as temperature is lowered, regardless of the exact values of the parameters. As shown in Fig. 3(a),  $C$  behaves similarly to the interlayer correlation length [Fig. 2(d)] for temperatures not too far from the onset of the stripe orders. Figure 3(b) shows the real-space configurations for regime I and II. In regime I, there exists no, or very weak, in-plane charge order and the correlation between layers is small. In regime II, charge stripe order develops while the spins remain disordered. Out-of-plane charge correlation develops to minimize the Coulomb repulsion. In regime III, the spin order develops and the out-of-plane charge correlation is suppressed and we expect the system goes into a three-layer stacking as described in Ref. [20].

Intuitively, this curious rise and fall of interlayer correlation is a result of two competing interactions [24]. The interlayer charge-charge coupling favors the stripes in different layers to be out of phase because the charge stripes repel each other, while the interlayer charge-spin coupling favors in-phase stripes because the formation of in-plane spin modulation causes the dissipation of kinetic energy of the electrons. In-plane charge order appears first, resulting in the buildup

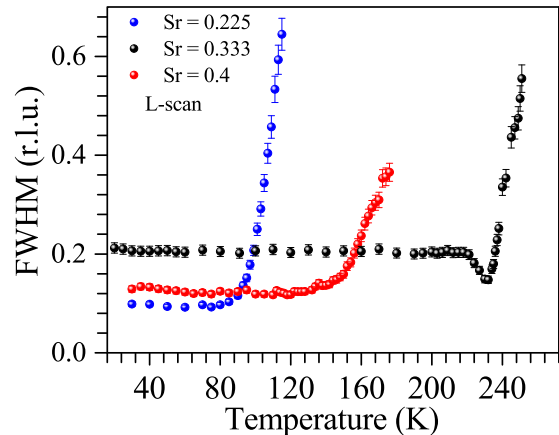


FIG. 4. (Color online) Peak widths of charge stripes with different hole concentrations. The data were taken from single crystals ( $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ ) with different hole concentrations, i.e.,  $x = 0.225$ , 0.33, and 0.4. As can be seen, the inverse order-disorder transition occurs only for  $x = 0.33$ .

of an out-of-phase interlayer charge correlation, but as the in-plane spin-stripe order starts to develop, the interlayer charge order is suppressed.

Figure 4 shows the measurements at doping concentrations  $x = 0.225, 0.33$ , and 0.4; only at  $x = 0.33$  does the inverse transition occur. This phenomenon adds to the list of anomalies for  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  due to the commensurate pinning of the charges to the Ni lattice at  $x = 0.33$  [20,25–28]. For  $x \neq 0.33$ , topological defects, such as dislocations and kinks, can easily proliferate to destabilize the in-plane charge stripe order [29,30]. This also weakens the phase-dependent interlayer charge-spin couplings in Eq. (2); as a result, there are no competing interlayer interactions to cause the inverse transition of the interlayer correlation.

Our work points to the importance of the interlayer coupling in LSNO. However, it is worth noting that, using x-ray scattering on the family compounds  $\text{Pr}_{1-x}\text{Sr}_x\text{NiO}_4$  (PSNO) and  $\text{Nd}_{1-x}\text{Sr}_x\text{NiO}_4$  (NSNO), Hücker *et al.* [21] points out that a stacking fault of  $\text{NiO}_2$  layers can induce a minimum of the correlation length of charge stripes along the  $c$  axis just below the transition temperature. Compared with PNSO and NSNO, LSNO shows no orthorhombic strain, so the stacking fault is expected to have the less effect on governing the interlayer coupling, however, the similar behavior for spin stripes would be expected if the stacking fault of  $\text{NiO}_2$  layers is the major driving force for the formation of inverse order-disorder. Interlayer Coulomb interaction has been argued to be crucial in understanding an anomalous shrinking of the  $c/a$  lattice parameter ratio that correlates with  $T_{CO}$  in  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  [20], as well as the existence of fluctuating charge stripes that persist to high temperatures [20,22]. In particular, the inverse order-disorder transition of the interlayer charge order observed in this work may provide a new direction to understand the dominance of the dynamical stripes in cuprates. Further extension of the current work to study the dynamical interlayer correlations in  $\text{La}_{1.67}\text{Sr}_{0.33}\text{NiO}_4$  [20,31] and its sister compound  $\text{La}_{1.67}\text{Sr}_{0.33}\text{CoO}_4$  [32,33] may help

to elucidate the unusual transport behavior caused by the charge/spin stripes in the transition metal oxides.

### ACKNOWLEDGMENTS

We acknowledge many stimulating discussions with Professor Cheng-Hsuan Chen and Professor Bruce Gaulin. We are grateful to Ministry of Science and Technology in Taiwan for the financial support through Grants No. 99-2112-M-032-005-MY3 and No. 102-2112-M-032-004-MY3 (C.H.D.), and No. 102-2112-M-002 -003 -MY3 (Y.J.K.).

### APPENDIX A: CHARGE AND MAGNETIC CORRELATIONS

Synchrotron x-ray scattering experiments were carried out on the beam lines BL07 and SP12B1 of NSRRC, Taiwan. The sample was mounted on a closed-cycle cryostat mounted on a multicircle diffractometer, which allows the scans to be performed along any of the reciprocal space crystallographic axes,  $H(=2\pi/a)$ ,  $K(=2\pi/b)$ , and  $L(=2\pi/c)$ . Throughout this study for  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$ , a tetragonal unit cell with lattice parameters of  $a = b = 5.4145 \text{ \AA} = 2\sqrt{2}d_{\text{Ni-O}}$  and  $c = 12.715 \text{ \AA}$  was used to index the reflections. There was no realignment of the crystal during the measurements because  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$  does not display any structural phase transitions at low temperatures [20]. The incident x-ray energy was set to 10 keV by a pair of high-quality single crystals of Si(1 1 1), and a LiF crystal was used in an analyzer to define the scattered x rays from the sample. The experimental

resolution function was determined to be  $\epsilon_H^{-1} \sim 0.0019 \text{ \AA}^{-1}$ ,  $\epsilon_K^{-1} \sim 0.001 \text{ \AA}^{-1}$ , and  $\epsilon_L^{-1} \sim 0.015 \text{ \AA}^{-1}$  as measured on the Bragg peak (4 0 0), which is near the charge-ordering peaks measured at  $T = 140 \text{ K}$ , and the sample mosaic width was found to be  $\sim 0.02^\circ$ . The peak profiles of the Bragg reflection (4 0 0) were monitored throughout the measurements and showed no changes. The correlation lengths of the charge-stripe reflections were extracted from their measured peak profiles convoluted with the resolution functions, and the error bars shown in this study were taken from the square root of the data points. Measurements were taken as a function of temperature through the Bragg peak and charge-stripe satellites along the crystallographic axes of  $H$ ,  $K$ , and  $L$  in the reciprocal space.

Figure 5 shows how the peak widths of the charge modulation along the  $H$  and  $K$  directions change as a function of temperature. As can be seen, for temperatures above  $T_{CO}$ , the charge modulation is isotropic in the  $a \times b$  plane, but as temperature is lowered, there is an anisotropic evolution of the correlation lengths. Figure 6 displays the evolution of the peak profile of charge modulation along  $c$  axis as a function of temperature. As temperature is decreased, the peak narrows at first, indicating an increase in order along the  $c$  axis, but then it widens again, indicating an inverse order-disorder transition.

For the study of spin stripes, in order to enhance the signals from the spin modulations, a resonant soft x-ray diffraction experiment was conducted on the beam line BL05B3 of NSRRC. The measurements were performed to scan the spin-stripe reflection (0.66 0 0) through the  $L$  edge of Ni.

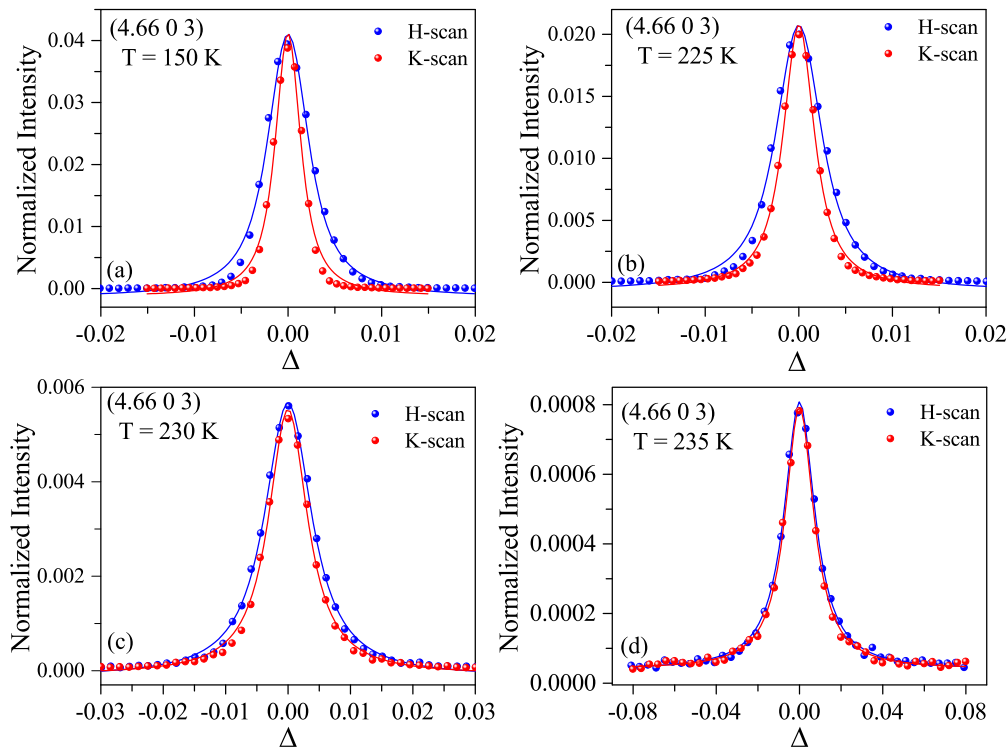


FIG. 5. (Color online) Comparison of the peak profiles along the  $H$  and  $K$  directions at different temperatures. In order to compare the peak profiles along the  $H$  and  $K$  directions, the central positions of the charge-stripe reflection (4.66 0 3) are set to zero. (a) Below temperature  $T \sim 218 \text{ K}$ , the ratio of peak widths along  $H$  and  $K$  directions is almost constant. (b) and (c) Upon warming, the ratio changes as a function of temperature, (d) approaching 1 as the temperature approaches  $T_{CO}$  ( $\sim 238 \text{ K}$ ).

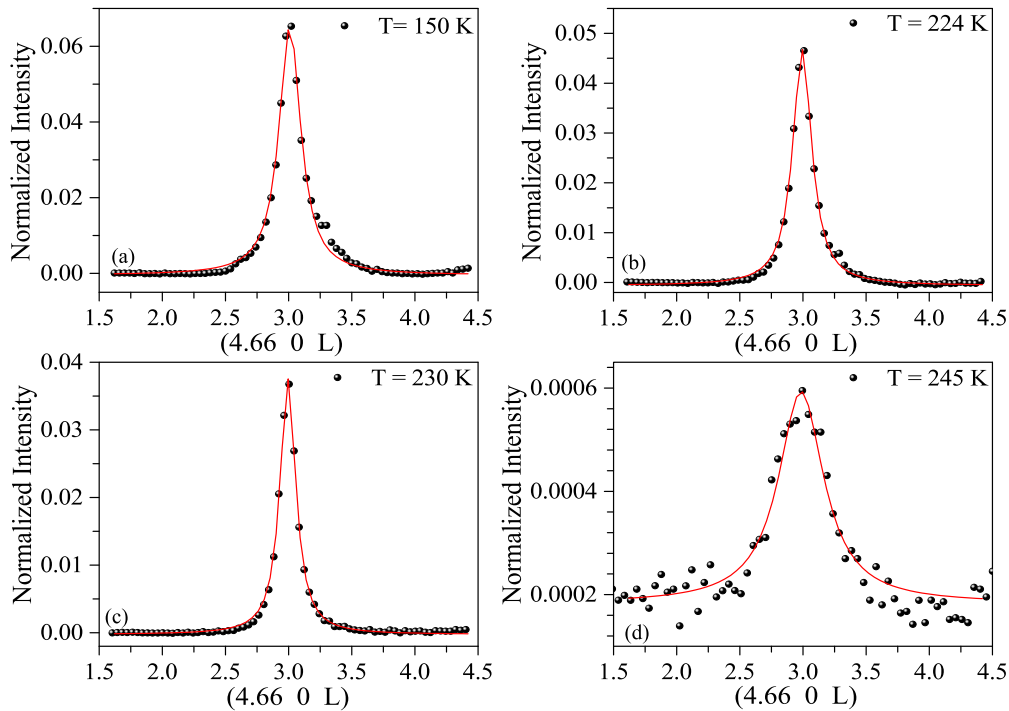


FIG. 6. (Color online) Peak profiles of a charge stripe reflection along the  $L$  direction at different temperatures. Scans through the  $L$  direction ( $c$  axis) of the charge-stripe reflection (4.66 0 3) at (a) 150 K, (b) 224 K, (c) 230 K, and (d) 245 K are shown. As temperature is lowered, the peak narrows and becomes sharpest at  $\sim 230$  K, but it then widens below 230 K, indicating an inverse order-disorder transition.

A large resonance from the spin reflection was observed at the  $L_3$  edge of Ni with incident  $\pi$ -polarized x rays at  $T = 80$  K. Upon warming, the spin ordering reflection was observed to persist at  $T = 230$  K as shown in Fig. 7.

**APPENDIX B: THERMAL HYSTERESIS**

Experiments were also conducted to study thermal effects on the charge modulation. The measurement was done on a second crystal of  $\text{La}_{5/3}\text{Sr}_{1/3}\text{NiO}_4$ . As shown in Fig. 8,

charge stripes show a hysteresis behavior around the transition boundary under different thermal treatments. This is in accordance with previously described thermal phenomena of an electron liquid crystal [34,35]. The data shown in Fig. 8 were collected during three sequences of warming and cooling. The sample was first cooled down to 130 K from room temperature in approximately two hours, and after the alignment at 130 K, the data (as marked by blue triangles in Fig. 8) were collected by increasing temperature and scanning the charge-stripe

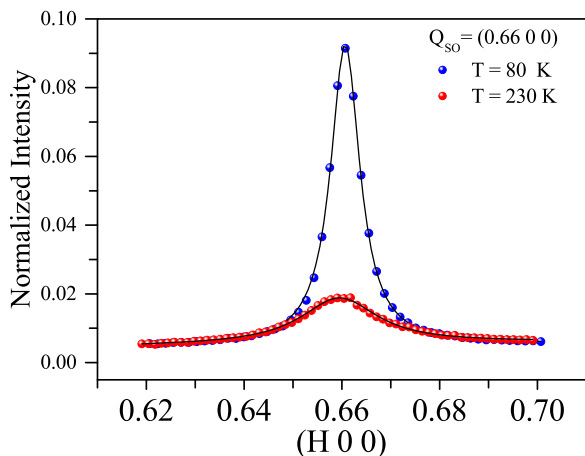


FIG. 7. (Color online) Spin-stripe reflection (0.66 0 0) at  $T = 80$  and 230 K. The data were collected by using resonant soft x-ray diffraction at Ni  $L_3$  edge along the  $a$  axis. The black lines are the best fits with a Lorentzian function.

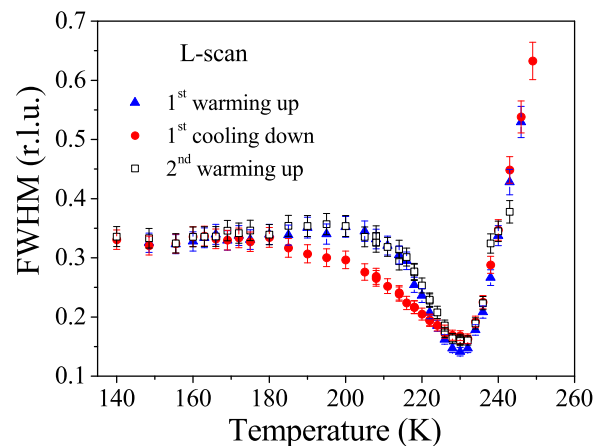


FIG. 8. (Color online) Thermal effects on the charge-stripe modulations. Evolution of the peak width (FWHM) of the charge-stripe reflection (4.66 0 3) along the  $L$  direction is shown as a function of temperature for the different thermal processes. As can be seen, there is some thermal hysteresis.

reflection (4.66 0 3) along the  $H$ ,  $K$ , and  $L$  directions as a function of temperature until  $T = 250$  K, where the reflection becomes very broad and weak. The sample was then warmed up to 260 K and kept at that temperature for approximately

half an hour, after which measurements (marked by red dots) were taken as the sample was cooled to  $T = 140$  K. A third round of measurements (marked by open squares) were taken as the sample was warmed up to 250 K once more.

- 
- [1] P. A. Lee, Naoto Nagaosa, and Xiao-Gang Wen, *Rev. Mod. Phys.* **78**, 17 (2006).
- [2] J. M. Tranquada, B. J. Sternlieb, J. D. Axe, Y. Nakamura and S. Uchida, *Nature (London)* **375**, 561 (1995).
- [3] G. Ghiringhelli *et al.*, *Science* **337**, 821 (2012).
- [4] J. M. Tranquada, G. D. Gu, M. Hcker, Q. Jie, H.-J. Kang, R. Klingeler, Q. Li, N. Tristan, J. S. Wen, G. Y. Xu, Z. J. Xu, J. Zhou, and M. v. Zimmermann, *Phys. Rev. B* **78**, 174529 (2008).
- [5] S. A. Kivelson, I. P. Bindloss, E. Fradkin, V. Oganesyan, J. M. Tranquada, A. Kapitulnik, and C. Howald, *Rev. Mod. Phys.* **75**, 1201 (2003).
- [6] E. Fradkin, S. A. Kivelson, M. J. Lawler, J. P. Eisenstein, and A. P. Mackenzie, *Ann. Rev. Cond. Mat. Phys.* **1**, 153 (2010).
- [7] S. A. Kivelson, E. Fradkin, and V. J. Emery, *Nature (London)* **393**, 550 (1998).
- [8] M. Vojta, *Adv. Phys.* **58**, 699 (2009).
- [9] J. M. Tranquada, H. Woo, T. G. Perring, H. Goka, G. D. Gu, G. Xu, M. Fujita, and K. Yamada, *Nature (London)* **429**, 534 (2004).
- [10] V. Hinkov, D. Haug, B. Fauqué, P. Bourges, Y. Sidis, A. Ivanov, C. Bernhard, C. T. Lin, and B. Keimer, *Science* **319**, 597 (2008).
- [11] R. M. Fernandes, A. V. Chubukov, and J. Schmalian, *Nature Phys.* **10**, 97 (2014).
- [12] T.-M. Chuang, M. P. Allan, Jinho Lee, Yang Xie, Ni Ni, S. L. Bud'ko, G. S. Boebinger, P. C. Canfield, and J. C. Davis, *Science* **327**, 181 (2010).
- [13] E. Berg, E. Fradkin, E.-A. Kim, S. A. Kivelson, V. Oganesyan, J. M. Tranquada, and S. C. Zhang, *Phys. Rev. Lett.* **99**, 127003 (2007).
- [14] W. Hu, S. Kaiser, D. Nicoletti, C. R. Hunt, I. Gierz, M. C. Hoffmann, M. Le Tacon, T. Loew, B. Keimer, and A. Cavalleri, *Nature Mater.* **13**, 705 (2014).
- [15] P. G. Freeman, A. T. Boothroyd, D. Prabhakaran, M. Enderle, and C. Niedermayer, *Phys. Rev. B* **70**, 024413 (2004).
- [16] S. H. Lee, and S.-W. Cheong, *Phys. Rev. Lett.* **79**, 2514 (1997).
- [17] S. Anissimova, D. Parshall, G. D. Gu, K. Marty, M. D. Lumsden, Songxue Chi, J. A. Fernandez-Baca, D. L. Abernathy, D. Lamago, J. M. Tranquada, and D. Reznik, *Nature Commun.* **5**, 3467 (2014).
- [18] S. H. Lee, J. M. Tranquada, K. Yamada, D. J. Buttrey, Q. Li, and S.-W. Cheong, *Phys. Rev. Lett.* **88**, 126401 (2002).
- [19] R. J. Cava, B. Batlogg, T. T. Palstra, J. J. Krajewski, W. F. Peck, A. P. Ramirez, and L. W. Rupp, *Phys. Rev. B* **43**, 1229 (1991).
- [20] A. M. Milinda Abeykoon, E. S. Božin, Wei-Guo Yin, Genda Gu, John P. Hill, John M. Tranquada, and Simon J. L. Billinge, *Phys. Rev. Lett.* **111**, 096404 (2013).
- [21] M. Hücker, M. v. Zimmermann, and G. D. Gu, *Phys. Rev. B* **74**, 085112 (2006).
- [22] C.-H. Du, M. E. Ghazi, Y. Su, I. Pape, P. D. Hatton, S. D. Brown, W. G. Stirling, M. J. Cooper, and S.-W. Cheong, *Phys. Rev. Lett.* **84**, 3911 (2000).
- [23] O. Zachar, S. A. Kivelson, and V. J. Emery, *Phys. Rev. B* **57**, 1422 (1998).
- [24] E. P. Rosenthal, E. F. Andrade, C. J. Arguello, R. M. Fernandes, L. Y. Xing, X. C. Wang, C. Q. Jin, A. J. Millis, and A. N. Pasupathy, *Nature Phys.* **10**, 225 (2014).
- [25] A. P. Ramirez, P. L. Gammel, S.-W. Cheong, D. J. Bishop, and P. Chandra, *Phys. Rev. Lett.* **76**, 447 (1996).
- [26] R. Kajimoto, T. Kakeshita, H. Yoshizawa, T. Tanabe, T. Katsufuji, and Y. Tokura, *Phys. Rev. B* **64**, 144432 (2001).
- [27] H. Yoshizawa, T. Kakeshita, R. Kajimoto, T. Tanabe, T. Katsufuji, and Y. Tokura, *Phys. Rev. B* **61**, R854(R) (2000).
- [28] K. Ishizaka, T. Arima, Y. Murakami, R. Kajimoto, H. Yoshizawa, N. Nagaosa, and Y. Tokura, *Phys. Rev. Lett.* **92**, 196404 (2004).
- [29] J. Li, Y. Zhu, J. M. Tranquada, K. Yamada, and D. J. Buttrey, *Phys. Rev. B* **67**, 012404 (2003).
- [30] J. Lloyd-Hughes, D. Prabhakaran, A. T. Boothroyd, and M. B. Johnston, *Phys. Rev. B* **77**, 195114 (2008).
- [31] W. S. Lee *et al.*, *Nature Commun.* **3**, 383 (2012).
- [32] A. T. Boothroyd, P. Babkevich, D. Prabhakaran, and P. G. Freeman, *Nature (London)* **471**, 341 (2011).
- [33] T. Lancaster, S. R. Giblin, G. Allodi, S. Bordignon, M. Mazzani, R. De Renzi, P. G. Freeman, P. J. Baker, F. L. Pratt, P. Babkevich, S. J. Blundell, A. T. Boothroyd, J. S. Möller, and D. Prabhakaran, *Phys. Rev. B* **89**, 020405 (2014).
- [34] E. W. Carlson and K. A. Dahmen, *Nature Commun.* **2**, 379 (2011).
- [35] Cheol Eui Lee and S. H. Yang, *J. Korean Phys. Soc.* **33**, L635 (1998).