

Cite this: *Dalton Trans.*, 2017, **46**, 10996

Pyridylpyrazole N^N ligands combined with sulfonyl-functionalised cyclometalating ligands for blue-emitting iridium(III) complexes and solution-processable PhOLEDs†

Helen Benjamin,^a Mark A. Fox,^a Andrei S. Batsanov,^a Hameed A. Al-Attar,^b Chensen Li,^c Zhongjie Ren,^c Andrew P. Monkman^b and Martin R. Bryce^a*

A series of blue iridium(III) complexes (**12–15**) comprising sulfonyl-functionalised phenylpyridyl cyclometalating ligands and pyridylpyrazole N^N ligands are reported, with an X-ray crystal structure obtained for **12**. The complexes are highly emissive with photoluminescence quantum yields of 0.52–0.70 in dichloromethane solutions: two of the complexes (**12** and **14**) show emissions at $\lambda_{\text{max}}^{\text{PL}}$ 457 nm which is considerably blue-shifted compared to the archetypal blue emitter Irpic (λ_{max} 468 nm). The short excited state lifetimes (1.8–3.3 μs) and spectral profiles are consistent with phosphorescence from a mixture of ligand-centred and MLCT excited states. Density functional (DFT) and time dependent DFT (TD-DFT) calculations are in agreement with the electrochemical properties and the blue phosphorescence of the complexes. The additional mesityl substituent on the pyridylpyrazole ligand of **12** and **13** enhances the solubility of the complexes facilitating thin film formation by solution processing. Phosphorescent organic light-emitting diodes (PhOLEDs) have been fabricated using **12** or **13** in a solution-processed single-emitting layer using either poly(vinylcarbazole) (PVK) or 1,3-bis(*N*-carbazolyl) benzene (mCP) as host. The most blue-shifted electroluminescence ($\lambda_{\text{max}}^{\text{EL}}$ 460 nm, CIE_{x,y} 0.15, 0.21) is obtained for an OLED containing complex **12** and mCP, with a brightness of 5400 cd m^{−2} at 10 V which is high for PhOLEDs with similar blue CIE coordinates using a solution-processed emitter layer.

Received 23rd June 2017,
Accepted 27th July 2017

DOI: 10.1039/c7dt02289a

rsc.li/dalton

Introduction

The varied applications of luminescent transition metal complexes¹ include biological labelling probes, ion sensors, water splitting, solar cells and emitters for phosphorescent organic light-emitting diodes (OLEDs)^{2–8} and for solid-state lighting.^{9,10} Cyclometalated iridium(III) complexes are especially prominent in the OLED field due to their ability to harvest both singlet and triplet excitons, which can result in internal quantum efficiencies approaching 100%.^{11–13} Many complexes incorporate cyclometalated 2-phenylpyridine (ppy) ligands where the highest occupied molecular orbital (HOMO) is loca-

lised mostly on the iridium atom and the phenyl ring, and the lowest unoccupied MO (LUMO) is on the pyridyl ring. This spacial separation of HOMO and LUMO means that the emission wavelength of the complexes, which occurs from a mixture of triplet metal-to-ligand charge-transfer (³MLCT) states and π – π^* transitions of the ligands,^{14,15} can be tuned with precision by the presence of electron-withdrawing or electron-donating substituents at specific sites on the ppy framework. Additional attractive features are that the complexes generally emit with high quantum yields and relatively short excited state lifetimes on the microsecond timescale, and they possess high photochemical and chemical stability.^{11–13}

Blue emitting iridium complexes are important current targets.^{16,17} Four main approaches are known to be effective in shifting the emission of iridium complexes towards the blue.¹⁸ These are: (1) Lowering the HOMO with respect to the LUMO by introducing electron-withdrawing groups, such as fluorine¹⁹ sulfonyl,²⁰ phosphoryl,²⁰ perfluoroalkyl,²¹ perfluoroalkyl carbonyl,²² and cyano¹³ substituents at specific positions on the phenyl ring. (2) Raising the LUMO by either adding electron-donating groups such as methoxy to the pyridyl ring,^{23,24} or replacing the pyridyl ring with another heterocycle with higher

^aDepartment of Chemistry, Durham University, Durham DH1 3LE, UK.
E-mail: m.r.bryce@durham.ac.uk

^bDepartment of Physics, Durham University, Durham DH1 3LE, UK

^cState Key Laboratory of Chemical Resource Engineering, Beijing University of Chemical Technology, Beijing 100029, China

† Electronic supplementary information (ESI) available: Thermogravimetric data; NMR spectra; additional computational and CV data. CCDC 1495066. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c7dt02289a

LUMO energy.²⁵ (3) Using electron-withdrawing N^N ligands, *e.g.* pyridyl-azole, to modulate the electron density around the metal centre, thereby affecting the HOMO energy.^{26–28} (4) Using strong σ -donor ligands, *e.g.* carbenes, to increase the crystal field splitting, thereby widening the HOMO–LUMO gap and shifting non-emissive d–d* metal-centred (MC) states to higher energies.¹⁹

The present study combines a pyridylpyrazole-based N^N ligand with sulfonyl-containing cyclometalating ligands²⁹ to obtain the new heteroleptic complexes **12–15** with emission blue-shifted compared to the archetypal blue emitter, FIrpic,¹⁶ and the analogous picolate-complexes **1** and **2**²⁹ (Fig. 1). Pyridylpyrazole ligands blue-shift the emission due to their high acidity, reducing the electron density around the Ir centre and hence reducing the HOMO level relative to the LUMO.³⁰ They have also been exploited as the chromophoric ligands in N-heterocyclic carbene complexes³¹ and in conjunction with other ligands.^{32–34} The strongly electron-withdrawing CF₃ group on the pyrazole ring should further blue shift the emission.³⁵ The *p*-tolylsulfonyl and methylsulfonyl groups (complexes **1** and **2**) both blue shift the emission to the same extent,²⁹ and methoxy substituents can lead to a blue shift depending on their position on the ppy ligand.^{36,37} Reducing the number of aromatic fluorine substituents, *e.g.* by selective replacement with methoxy, can maintain the blue colour and reduce chemical degradation of a complex during device operation.³⁸ Complexes **12–15** incorporate a mesityl substituent at C4 of the ppy ligand; it is known that a mesityl group at this position enhances the quantum yields of some complexes by reducing triplet–triplet quenching without affecting blue colour purity.^{39–42} We also report the new mesityl substituted pyridylpyrazole ligand **9** which achieves the desired aims of increasing the solubility of the complexes **12** and **13**, in com-

parison with **14** and **15**, thereby facilitating film formation by solution processes without affecting the emission colour.

Synthesis and characterisation

The route to ligand **9** is shown in Scheme 1. 2-Acetyl-4-chloropyridine **6** was synthesised by reaction between 4-nitro- α -picoline-*N*-oxide **3** and acetyl chloride to give **4**⁴³ in 23% yield. An intermediate oxime has been proposed in this step.⁴³ The *N*-oxide was reduced using PCl₃ to produce **5**⁴³ in 73% yield, followed by reaction with methyl magnesium chloride to give **6** in 92% yield.⁴⁴ The mesityl group was then introduced *via* a Suzuki coupling of **6** with 2,4,6-trimethylphenylboronic acid to give **7** in 52% yield. The final steps, described in the literature for other analogues,⁴⁵ involved a crossed Claisen condensation reaction with ethyl trifluoroacetate to give a presumed diketone intermediate **8**, followed by a ring closing condensation reaction with hydrazine hydrate to give **9** in 20% yield.

The desired complexes **12** and **13** were then synthesised under standard conditions;^{46,47} namely, reaction of the ligand **10** with IrCl₃·3H₂O and ligand **11**²⁹ with [Ir(COD)Cl]₂ in 2-ethoxyethanol to give a species presumed to be the bridged μ -dichloro diiridium dimer [Ir(L)₂Cl]₂. This intermediate species was then reacted *in situ* with ligand **9** to give the desired complexes **12** and **13** (Scheme 2). The attempted synthesis of **13** using IrCl₃·3H₂O failed to yield any product and the ligand **11** could not be recovered. Difficulties in the cyclometalation of ligands containing methoxy substituents using IrCl₃·3H₂O have been reported previously.^{29,36} Complexes **14** and **15** were synthesised from **10** and **11** by analogous reactions with 3-trifluoromethyl-5-(2-pyridyl)pyrazole ligand **16**.³⁰ Thermal gravimetric analysis (TGA) shows that all the complexes possess good thermal stability (Table S5 in ESI†), suggesting the complexes should be stable under device operation.

X-Ray crystal structure

The single crystal X-ray structure of the highly-functionalised complex **12** (Fig. 2) shows a distorted octahedral coordination of the Ir atom, similar to that in its analogues.³² The two Ir–C bonds are in *cis* positions to one another and *trans* to the Ir–N



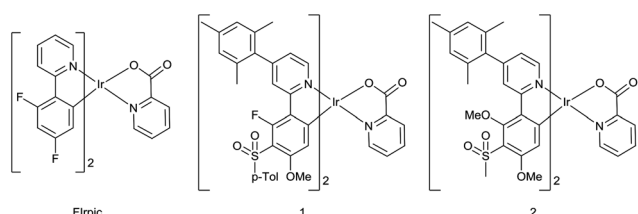


Fig. 1 Previously reported picolate complexes.



Scheme 1 Synthesis of ligand **9**. Reagents and conditions: i, CH₃COCl, 60 °C; ii, PCl₃, CHCl₃, reflux; iii, (1) CH₃MgCl, ether, 0 °C, (2) dilute HCl; iv, Pd(OAc)₂, PPh₃, 2,4,6-trimethylphenylboronic acid, Na₂CO₃, DME/water, reflux; v, KO^tBu, F₃CCO₂Et, THF, reflux; vi, N₂H₄·H₂O, ethanol, reflux.

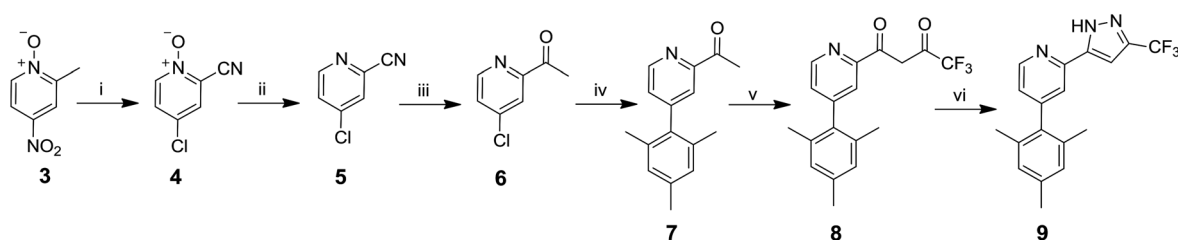

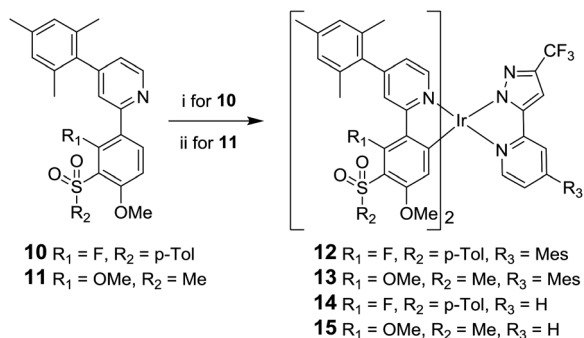

Scheme 2 Synthesis of complexes **12–15**. Reagents and conditions: i, $\text{IrCl}_3 \cdot 3\text{H}_2\text{O}$, 2-ethoxyethanol, 130 °C, followed by **9** (for **12** and **13**) or 3-trifluoromethyl-5-(2-pyridyl)pyrazole **16** (for **14** and **15**) DCM/ethanol, 55 °C; ii, $[\text{Ir}(\text{COD})\text{Cl}]_2$, 2-ethoxyethanol, 130 °C, followed by **9** or **16**, DCM/ethanol, 55 °C.

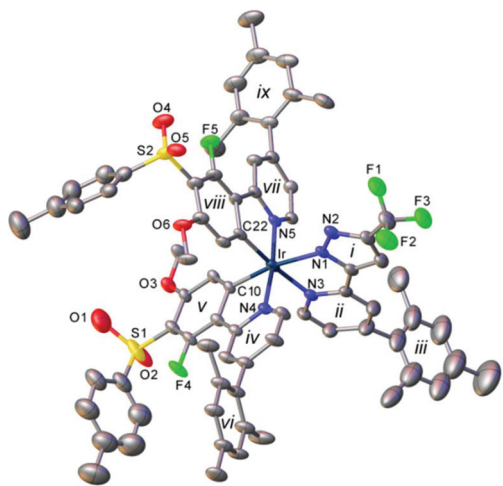


Fig. 2 X-ray molecular structure of **12**. H atoms and the disorder of CF_3 group are omitted; thermal ellipsoids are drawn at the 30% probability level. Bond distances (Å): Ir–N(1) 2.102(6), Ir–N(3) 2.142(8), Ir–N(4) 2.040(6), Ir–N(5) 2.057(6), Ir–C(10) 2.006(7) and Ir–C(22) 1.991(9). Interplanar angles (°): i/ii 7, ii/iii 90, iv/v 7, iv/vi 74, vii/viii 4, vii/ix 89.

bonds of the $\text{N}^{\wedge}\text{N}$ ligand, which are, therefore, elongated compared to the mutually *trans* bonds Ir–N(4) and Ir–N(5). The mesityl groups are near-perpendicular to the corresponding pyridyl rings. The crystal packing of **12** is dominated by edge-to-face contacts between arene groups, without π – π stacking.

Photophysical and electrochemical properties

The absorption and emission spectra of complexes **12–15** (Fig. 3) are consistent with pyridylpyrazole subtly lowering the energy of the HOMO. All the complexes show strong absorption bands in the 250–325 nm region, assigned to the π – π^* transitions on the ligands.^{16,18} Absorption bands with lower extinction coefficients in the 350–450 nm range are ascribed to singlet and triplet metal-to-ligand charge-transfer ($^1\text{MLCT}$ and $^3\text{MLCT}$) states.^{48,49} Here, we see differences between the picolinate complexes **1** and **2**,²⁹ and complexes **12–15**; the $^1\text{MLCT}$ bands move to higher energies on replacing the picolinate ligands with ligands **9** or **16**, suggesting the pyridylpyrazole has indeed decreased the energy of the metal d-orbitals. The emission spectra of the complexes are shown in Fig. 3b. Complexes **12–15** emit in the blue region, and display a similar emission profile to that of Firpic and the analogous picolinate complexes **1** and **2**. A notable feature is that the λ_{max} value for **12** and **13** is blue-shifted by 7 and 8 nm relative to their analogous picolinate complexes **1** and **2**, respectively. This represents a blue-shift of 11 nm and 2 nm relative to that of the benchmark sky-blue emitter Firpic.¹⁶ The impressive 11 nm shift for complex **12** is primarily a consequence of the combined benefits of the sulfone substituents and the $\text{N}^{\wedge}\text{N}$ ligand. The UV-Vis absorption and emission of complexes **14** and **15** are similar to those of complexes **12** and **13**, indicating the introduction of the mesityl substituent on the $\text{N}^{\wedge}\text{N}$ ligand does not impact the emission colour.

The photoluminescence quantum yield (PLQY) and lifetime data are listed in Table 1. The PLQYs for complexes **12–15** are comparable to their pic analogues **1** and **2**, with lifetimes and

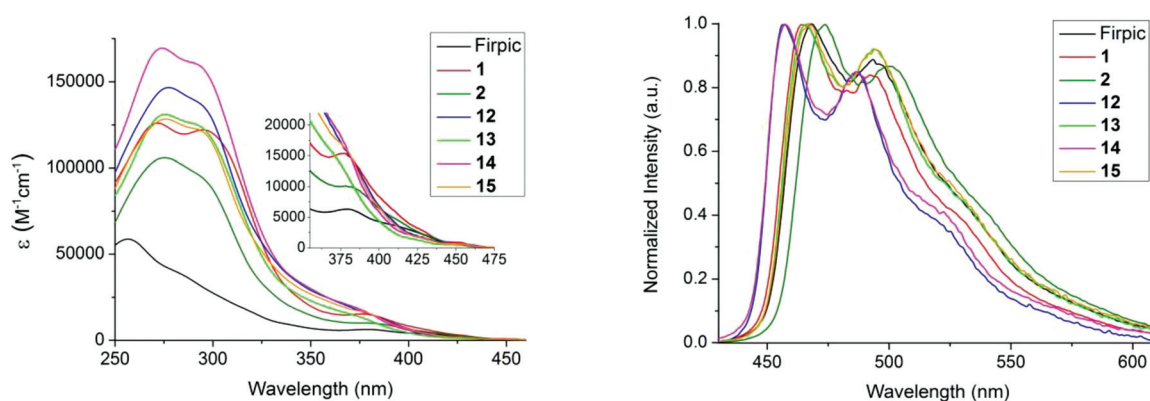


Fig. 3 (a) UV-Vis absorption spectra of the complexes in DCM [$<10^{-5}$ M]. Inset shows an expansion of the 350–475 nm region. (b) Emission spectra in deaerated DCM, $\lambda_{\text{ex}} = 380$ nm.



Table 1 Photophysical data for the iridium complexes

Complex	$\lambda_{\text{max}}^{\text{abs}} (\epsilon)^a/\text{nm} (\times 10^3 \text{ M}^{-1} \text{ cm}^{-1})$	$\lambda_{\text{max}}^{\text{em}}/ \text{nm}$	PLQY/ $\Phi_{\text{PL}}^{a,c}$	$\tau_{\text{P}}^{a,d}/\mu\text{s}$	$k_{\text{r}}/10^5 \text{ s}^{-1}$	$k_{\text{nr}}/10^5 \text{ s}^{-1}$
FIrpic	277 (50.1), 301 (34.2), 304 (32.6), 337 (13.8, sh), 357 (8.9, sh), 400 (6.2), 454 (0.8)	468, 496, 531 (sh)	0.67	1.72	3.90	1.92
1 ²⁹	258 (s sh, 108.5), 271 (128.6), 297 (123.4), 307 (sh, 112.5), 339 (s sh, 29.2), 379 (15.7), 450 (1.0)	464, 490, 524 (sh)	0.67	1.78	3.76	1.85
2 ²⁹	275 (104.4), 291 (101.9), 324 (sh, 47.8), 381 (14.5), 405 (sh, 7.9), 456 (0.9)	474, 497, 536 (sh)	0.58	2.13	2.72	1.97
12	274 (144.4), 293 (136.7), 370 (19.4), 419 (sh, 2.7), 447 (0.7)	457, 486, 521 (sh)	0.62	2.30	2.70	1.65
13	255 (sh, 100.4), 277 (125.8), 292 (133.5), 321 (59.6) (sh), 375 (16.3), 406 (sh, 5.1), 454 (0.8)	466, 494, 531 (sh)	0.52	3.13	1.66	1.53
14	274 (171.0), 291 (161), 374 (17.9), 418 (2.1), 450 (0.5)	457, 486, 522 (sh)	0.70	2.74	2.55	1.09
15	276 (129.3), 295 (122.75), 325 (50.8), 371 (18.2), 411 (3.2), 454 (0.7)	467, 494, 531 (sh)	0.64	3.30	1.94	1.09

^a Data obtained in DCM solution at 20 °C. ^b Data obtained in degassed DCM solution with $\lambda_{\text{ex}} = 380 \text{ nm}$. ^c Measured relative to Ir(ppy)₃ $\Phi_{\text{PL}} = 0.46$ in degassed DCM at 20 °C; estimated error $\pm 5\%$. ^d Estimated error $\pm 5\%$.

spectral profiles consistent with phosphorescence from a mixture of ligand-centred and MLCT excited states.^{18,49}

The electrochemical behaviour of complexes **12–15** was investigated by cyclic voltammetry (CV) in a 0.1 M NⁿBu₄PF₆ acetonitrile solution, and compared to FIrpic and picolinate analogues **1** and **2**.²⁹ The voltammograms of FIrpic, **12–15** are shown in Fig. 4 and S13,[†] and the key parameters are listed in Table 2. Whereas the picolinate complexes (FIrpic, **1** and **2**) show a single quasi-reversible oxidation wave, complexes **12–15** show two oxidation waves. In the case of **12** and **13** the two waves are irreversible, whereas for **14** and **15** the first oxidation wave is quasi-reversible.

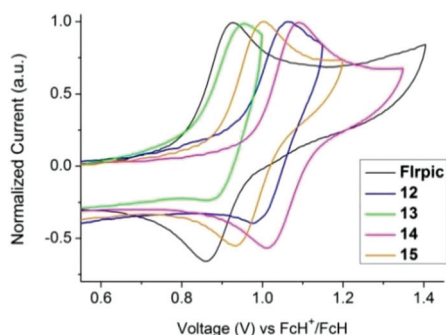


Fig. 4 Cyclic voltammograms of the iridium complexes.

Table 2 Cyclic voltammetric data of the iridium complexes

Complex	$E_{1/2}^{\text{ox1}}/ \text{V}$	$E_{1/2}^{\text{ox2}}/ \text{V}$	Obs $E(\text{HOMO})^c/ \text{V}$	Complex	Calc. HOMO/eV	Calc. LUMO/eV	Calc. HLG ^d /eV
FIrpic ²⁹	0.89	—	−5.69	FIrpic'	−5.49	−1.87	3.62
1 ²⁹	1.01	—	−5.81	1 '	−5.64	−1.94	3.70
2 ²⁹	0.89	—	−5.69	2 '	−5.53	−1.89	3.64
12	1.02 ^b	1.28 ^b	−5.82	12 '	−5.74	−1.83	3.91
13	0.91 ^b	1.17 ^b	−5.71	13 '	−5.62	−1.77	3.85
14	1.07	1.41 ^b	−5.87	14 '	−5.77	−1.89	3.88
15	0.97	1.28 ^b	−5.77	15 '	−5.64	−1.84	3.80

^a Redox data were obtained in 0.1 M NⁿBu₄PF₆ acetonitrile solutions and are reported vs. FcH/FcH⁺.⁵⁰ ^b Not reversible. ^c $E(\text{HOMO}) = -4.8 - E_{1/2}^{\text{ox1}}$ with respect to the FcH/FcH⁺ couple at 4.8 V. ^d HLG = HOMO–LUMO energy gap.

As complexes **12–15** contain a pyridylpyrazole-based ligand it is assumed the second oxidation occurs either on this ligand or is due to an interaction of this ligand with the metal. Exchanging the picolinate ancillary ligand for pyridylpyrazole results in an increase in the first oxidation potential by only 10–20 mV (**1** vs. **12**, **2** vs. **13**), consistent with pyridylpyrazole subtly lowering the energy of the HOMO. The presence of the mesityl group on the NⁿN ligand (complexes **12** and **13**) decreases the oxidation potentials by ca. 50 mV compared to the unsubstituted complexes **14** and **15**. No reduction waves were observed within the solvent window to −2.0 V. This is consistent with the calculated large HOMO–LUMO gap (Table 2).

Computations

Electronic structure calculations were carried out on the four new iridium complexes **12–15** to explore the frontier orbitals (Fig. 5 and Tables S1–S4[†]) in order to support the electrochemical and photophysical observations. The full geometries were optimised at B3LYP/LANL2DZ:3-21G* to compare directly with computed data of FIrpic, **1** and **2** reported earlier.²⁹ The optimised geometries are denoted as **12'–15'** to identify them as computed models and distinguish the predicted data from experimental data. Comparison between optimised (**12'**) and



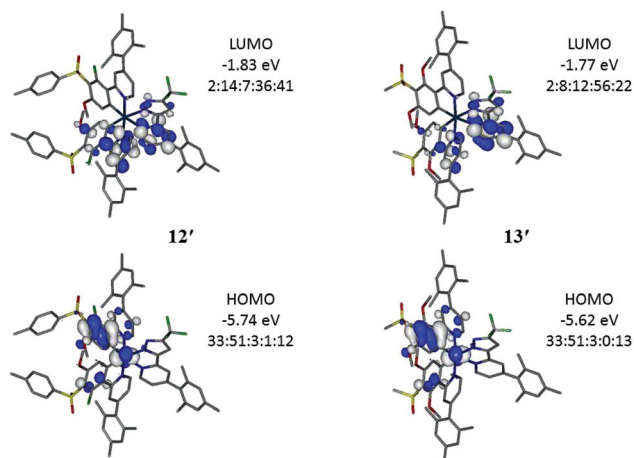


Fig. 5 Frontier molecular orbitals for **12'** and **13'**. All contours are plotted at ± 0.04 (e per bohr³)^{1/2}. Ir : phenyl : pyrazolyl : pyridyl (pypz) : pyridyl (ppy) % orbital contribution ratio are listed for each orbital.

X-ray determined (**12**) geometry reveals good agreement with differences in bond lengths below 0.04 Å.

Complexes **12'**–**15'** have HOMOs similar to FIrpic with the HOMO on iridium and phenyl (ppy) (Fig. 5). The lower HOMO energies on the complexes **12'**–**15'**, compared to FIrpic, reflect the electron-withdrawing properties of the sulfone groups. Frontier orbital energies for all complexes are listed in Table 2 for direct comparison with the observed CV data. The trends in observed and computed HOMO energies are in very good agreement. The iridium contributions (32–33%, Table 3) in the HOMOs of **12'**–**15'** are lower than the corresponding contribution in FIrpic' (44%) suggesting increased ligand contributions in the MLCT transitions involved in the emissions of **12'**–**15'** with respect to MLCT transitions for FIrpic'.

The LUMOs in **12'**–**15'** have substantial contributions from the pyridyl groups of the ppy and the pyridylpyrazole ligands which raise their orbital energies compared to FIrpic' where the LUMO is entirely located on the pyridyl group of the ppy ligands. The pyridylpyrazole ligands are, therefore, not ancillary. Consequently, the HOMO–LUMO energy gaps (HLGs) in complexes **12'**–**15'** are larger than the HLG in FIrpic' (Table 2)

Table 3 Iridium atom contributions in HOMOs and predicted (TD-DFT) emission wavelengths of iridium complexes

Complex	% Ir HOMO	$S_0 \leftarrow T_1^a$ /nm	Complex	Observed $\lambda_{\text{max}}^{\text{em}}$ ^b /nm
FIrpic' ²⁹	44	471	FIrpic	471
1' ²⁹	39	467	1	464
2' ²⁹	40	473	2	474
12'	33	455	12	457
13'	33	459	13	466
14'	32	454	14	457
15'	32	459	15	467

^a Values from TD-DFT data on S_0 optimised geometries with scaling energy factor of 0.945 based on DCM at 298 K. ^b Observed highest energy band from emission spectra (Table 1).

which is consistent with the observed blue-shifted emissions of **12**–**15** compared to FIrpic. The LUMOs in **13'** and **15'** contain more pyridylpyrazole character than ppy character (Fig. 5) which is explained by the increased number of electron-donating methoxy groups present in the ppy ligands of these complexes.

TD-DFT computations were carried out on the S_0 optimised geometries of **12'**–**15'** to predict emission wavelengths of these complexes. The initial excitation is assumed to give the lowest energy singlet excited state S_1 which in the presence of the iridium centre results in intersystem crossing (ISC) to form the triplet excited state T_1 and phosphorescence is observed from the $S_0 \leftarrow T_1$ process. The small Stokes shifts observed for these complexes suggest that the T_1 geometry is similar to the corresponding S_0 geometry. The reverse process $S_0 \leftarrow T_1$ is thus considered to have the same nature as the computed $S_0 \rightarrow T_1$ process with the predicted emission wavelength adjusted to take into account the Stokes shift. Table 3 shows there is close agreement between the predicted $S_0 \leftarrow T_1$ wavelengths and the observed emission wavelengths for all the complexes.

Phosphorescent organic light-emitting devices

PhOLEDs containing complex **12**, **13** or **2** as the dopant complex were fabricated to compare directly with our reference devices containing FIrpic and **1**. The initial standard device architecture comprised of a simple single-emissive-layer which was a blend of poly(vinylcarbazole) (PVK) as the host material, OXD-7 (an electron-transporting material) and the Ir complex to give the architecture: ITO/PEDOT:PSS (45 nm)/PVK:OXD-7 (30 wt%):Ir complex (15 wt%) (60 nm)/TPBi (30 nm)/LiF (1 nm)/Al (100 nm). The emissive layer was spin-coated from chlorobenzene solution to prevent possible degradation of the complexes which is known to occur during thermal evaporation of complexes which have fluorinated ligands.^{38,51–54} TPBi was used as an additional electron transporting layer adjacent to the cathode to improve charge balance and to ensure that excitons are confined in the emitter layer.⁵⁵ The efficiency and luminance data of the devices are summarised in Table 4 and the electroluminescence (EL) spectra are shown in Fig. 6a. The EL and PL spectra are similar for all the complexes due to efficient exciton confinement on the emissive molecules. The $\lambda_{\text{max}}^{\text{EL}}$ of complex **12** is significantly bluer (by 6 nm) than the corresponding pic complex **1**. However, as a trade-off, **12** has lower brightness (panel e), lower EQE (panel c), and lower current and power efficiencies (panels d and f). Based on the electrochemical data, the HOMO of **12** is lower in energy than **1**, which could be partially responsible for the reduced performance. Complex **13**, however, performed better than **2**, with comparable brightness and turn-on voltage (panel e), and with superior EQE, current and power efficiencies. The $\lambda_{\text{max}}^{\text{EL}}$ of **13** is also blue-shifted relative to **2**; however, this is offset by a broader emission resulting in similar CIE coordinates for both complexes. The additional mesityl substituent on the N^N



Table 4 Summary of device data

Complex	$\lambda_{\text{max}}^{\text{EL}}/\text{nm}$	Brightness (max, and at 10 V)/ cd m^{-2}	Turn-on voltage ^c /V	EQE _{max} ^a /%	Current efficiency/ cd A^{-1}	Power efficiency/ lm W^{-1}	CIE coordinates/(x,y) ^d
Flrpic ^a	475	7340, 2380	6.2	5.4	12.2	5.1	(0.19, 0.38)
1 ^a	470	2072, 175	8.5	3.5	6.1	1.9	(0.16, 0.30)
2 ^a	478	516, 160	8.5	1.2	2.6	0.9	(0.22, 0.40)
12 ^a	464	1066, 55	9.5	2.3	4.1	1.2	(0.17, 0.28)
13 ^a	473	456, 195	7.9	1.7	3.9	1.4	(0.23, 0.40)
12 ^b	460	5428, 5400	6.2	6.3	6.9	3.5	(0.15, 0.21)

^a In PVK host. ^b In mCP host. ^c Measured at a brightness of 10 cd m^{-2} . ^d Measured at 12 V.

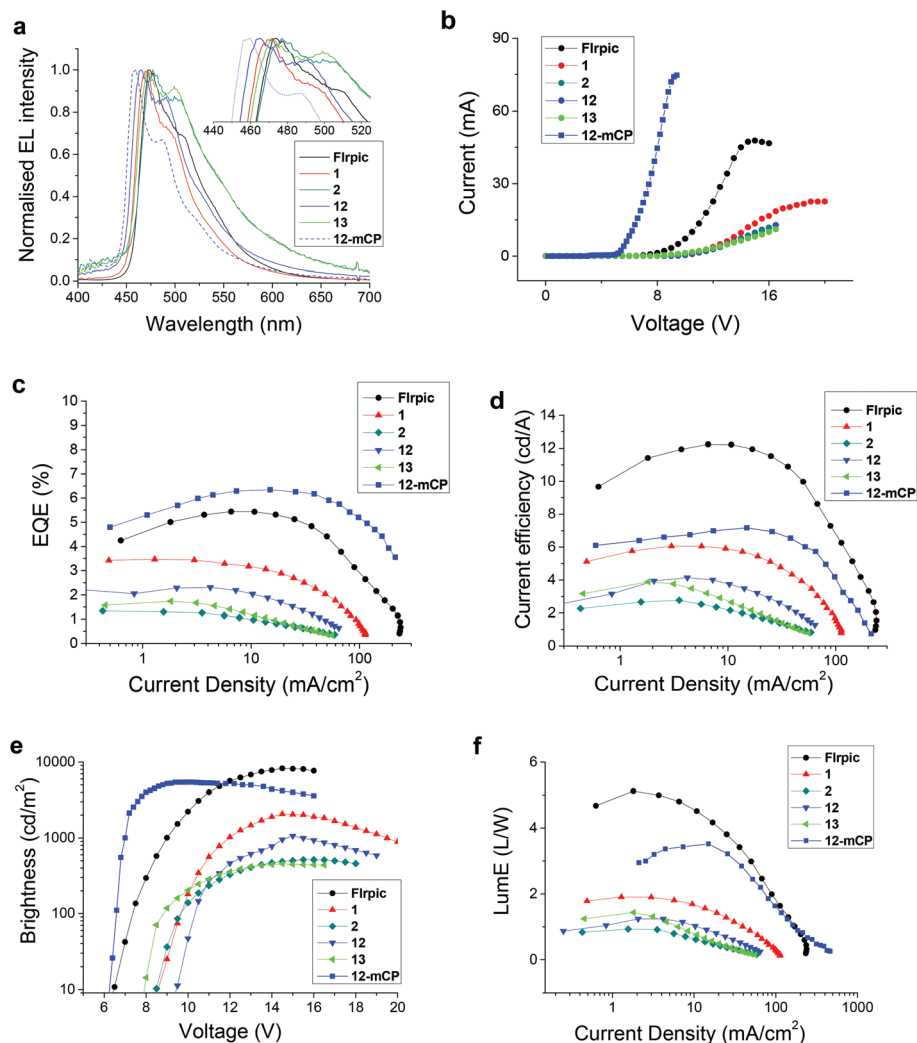


Fig. 6 Electroluminescent device data for complexes Flrpic, 1, 2, 12 and 13 in PVK host and for 12 in mCP host.

ligand of **12** and **13** enhances the solubility of the complexes facilitating thin film formation by solution processing.

We further explored the bluest complex **12** using mCP as a wide energy gap host which is more appropriate for a deep blue emitter in the architecture: ITO/TAPC (45 nm)/mCP:Ir complex **12** (15 wt%) (45 nm)/Tm3PyBP (5 nm)/TPBi (30 nm)/LiF (1 nm)/Al (100 nm). TAPC served as a hole-transporting

layer and Tm3PyBP serves as an additional hole/exciton-blocking layer to optimise the device structure.⁵⁶ Compared to the **12**:PVK device, the **12**:mCP device displayed a significantly lower turn-on voltage and further blue shifted electroluminescence to $\lambda_{\text{max}}^{\text{EL}}$ 460 nm, CIE_{x,y} (0.15, 0.21) with an increased maximum EQE of 6.3% and increased brightness at 10 V of 5400 cd m^{-2} which is high compared to reported PhOLEDs



with similar blue CIE coordinates using a solution-processed emitter layer.⁵⁷

Conclusions

To summarise, replacing the picolinate ancillary ligand of the heteroleptic iridium complexes **1** and **2** with a pyridylpyrazole-based ligand affords the new complexes **12–15** with blue shifted emission. This is ascribed to a reduction of electron density around the metal centre which results in a lowering of the energy of the HOMO of the complexes, as observed in the solution electrochemical data. (TD-)DFT calculations are in excellent agreement with the observed photophysical and electrochemical properties of the complexes. Blue-emitting PhOLEDs have been fabricated with a solution-processed emissive layer structure. Notably, devices of complex **12** possess $\lambda_{\text{max}}^{\text{EL}}$ 460 nm and CIE_{x,y} (0.15, 0.21) with brightness at 10 V of 5400 cd m⁻². This study demonstrates that the rational design of new complexes with specific functionalities on the cyclometalating and the N[^]N ligands is an effective route to new efficient blue emitters and PhOLEDs using relatively simple device architectures.

Experimental section

Materials, synthesis and characterisation

All commercially available chemicals were used without further purification. Reactions requiring an inert atmosphere were performed under a blanket of argon gas, which was dried over a phosphorus pentoxide column. Anhydrous solvents were dried through an HPLC column on an Innovative Technology Inc. solvent purification system. Column chromatography was performed using 40–60 μm mesh silica gel. Analytical TLC was performed on plates pre-coated with silica gel (Merck, silica gel 60F254) and visualised using UV light (254, 315, 365 nm). NMR spectra were recorded on a Bruker Avance 400 MHz spectrometer. Chemical shifts are referenced to tetramethylsilane [TMS, Si(CH₃)₄] at 0.00 ppm. Melting points were determined in open-ended capillaries using a Stuart Scientific SMP3 melting point apparatus at a ramping rate of 1 °C min⁻¹ and were recorded to the nearest 0.1 °C. ESI and MALDI mass spectra were recorded on a Thermo-Finnigan LTQ FT (7.0 T magnet) spectrometer. ASAP mass spectra were recorded on a Waters Xevo QTOF spectrometer. GCMS spectra were recorded on a Thermo-Finnigan Trace GCMS (EI and CI ion sources). Elemental analyses were obtained on an Exeter Analytical Inc. CE-440 elemental analyzer.

Solution electrochemistry and photophysics

Cyclic voltammetry experiments were recorded using a BAS CV50 W electrochemical analyzer fitted with a three-electrode system consisting of a Pt disk ($\varnothing = 1.8$ mm) as the working electrode, a Pt wire as an auxiliary electrode and an Ag/AgNO₃ (0.1 M [NEt₄][ClO₄] in CH₃CN) system as the reference elec-

trode. Experiments were conducted in dry acetonitrile solution with N[^]Bu₄PF₆ (0.1 M) as the supporting electrolyte at a scan rate of 100 mV s⁻¹. The reference electrode was assumed to be stable and was referenced externally to ferrocene (Cp₂Fe) and decamethylferrocene (Cp*₂Fe) which displayed potentials ($E_{1/2}$) of -0.41 V and +0.10 V, respectively, *versus* Ag/AgNO₃ under these conditions. It was not possible to use Cp₂Fe or Cp*₂Fe as an internal reference because their addition to the solutions of the complexes resulted in a distortion of the redox waves of the complexes.

Solution state photophysical data were obtained using freshly prepared solutions of the complexes in DCM. Emission and lifetime measurements used thoroughly degassed solutions achieved by three freeze-pump-thaw cycles, and quartz cuvettes with a path length of 1 cm. The solutions had absorbance below 0.10 to minimise inner filter effects. UV-vis absorption measurements were recorded using a Unicam UV2-100 spectrometer operated with Unicam Vision (ver. 3.50) software. Baseline correction was achieved by reference to pure solvent in the same cuvette. Absorption measurements were obtained using quartz cuvettes with a path length of 2 cm. Excitation and emission spectra were recorded on a Jobin-Yvon-Horiba SpexFluoromax 3 Spectrometer. Solutions of the complexes in degassed DCM [$<10^{-5}$ M] were used for decay measurements. Samples were excited with a pulsed nitrogen laser emitting at 337.1 nm. Emission was focused onto a spectrograph and detected on a sensitive gated iCCD camera (Stanford Computer Optics) with sub-nanosecond resolution. Solution PLQYs were recorded in degassed solvent, and determined using the relative method, with Ir(ppy)₃ ($\Phi_{\text{PL}} = 0.46$ in degassed dichloromethane, determined in-house *vs.* $\Phi_{\text{PL}} = 0.546$ in 0.5 M H₂SO₄) as the reference. The PLQYs were calculated according to the following equation:

$$\Phi_{\text{x}} = \Phi_{\text{ref}} \frac{\text{Grad}_{\text{x}}}{\text{Grad}_{\text{ref}}} \left(\frac{\eta_{\text{x}}}{\eta_{\text{ref}}} \right)^2$$

where subscripts 'x' and 'ref' denote the material being measured and the reference, respectively. Φ represents the PLQY, Grad is the gradient from the plot of integrated fluorescence intensity *vs.* absorbance, and η is the refractive index of the solvent.

Thermal analyses

Thermogravimetric analysis (TGA) was performed in a nitrogen atmosphere using a PerkinElmer Pyris 1 TGA instrument. The complexes were heated at a rate of 10 °C min⁻¹ from room temperature up to 600 °C.

Computational studies

All calculations were carried out with the Gaussian 09 package.⁵⁸ All optimised S₀ geometries for **12'–15'** were carried out using B3LYP⁵⁹ with the pseudopotential (LANL2DZ)⁶⁰ for iridium and 3-21G* basis set for all other atoms.⁶¹ This model chemistry was selected for direct comparison with computed data on FIrpic', **1'** and **2'**.²⁹ Electronic structure and TD-DFT



calculations were also from the optimised geometries at B3LYP/LANL2DZ:3-21G*. The MO diagrams and orbital contributions were generated with the aid of Gabedit⁶² and GaussSum⁶³ packages, respectively.

Phosphorescent organic light-emitting devices (PhOLEDs)

PhOLEDs with poly(vinylcarbazole) (PVK) host were fabricated on indium tin oxide (ITO)-coated glass substrates of thickness 125 nm and possessing a sheet resistance of 15 Ω per square. Poly(3,4-ethylenedioxythiophene) doped with high work function hole injection layer poly(styrenesulfonic acid) (PEDOT: PSS) (HIL1.3) from CLEVIOS was spin-coated at 2500 rpm for 60 s to produce a \sim 50 nm thick hole-injecting/transporting layer (HTL). The PEDOT:PSS layer was annealed at *ca.* 200 $^{\circ}$ C for 5 min to remove any residual water. A chlorobenzene solution of 25 mg mL⁻¹ of poly(vinylcarbazole) (PVK) (M_w = 90 000) was doped with 30% w/w of (1,3-phenylene)bis[5-(4-*tert*-butyl-phenyl)-1,3,4-oxadiazole] (OXD-7). Blended devices were made by mixing 15% w/w of the Ir complexes. The prepared mixtures were filtered with a 0.45 μ m pore filter and spin-coated at 2500 rpm for 1 min on the top of the PEDOT:PSS layer and baked for 10 min at 120 $^{\circ}$ C. Each sample was shadow masked to produce four identical devices of area 4 \times 5 mm; the samples were then introduced into a nitrogen glove box, where 30 nm of 2,2',2''-(1,3,5-benzenetriyl)tris-[1-phenyl-1H-benzimidazole] (TPBi) was evaporated as an electron injection/hole blocking layer at a rate of \sim 1 A s⁻¹ under vacuum at a pressure of *ca.* 1 \times 10⁻⁶ Torr, followed by 0.8 nm LiF and a 100 nm capping layer of aluminium under the same evaporation conditions. Therefore, the device configuration for all complexes was: ITO/PEDOT:PSS (50 nm)/PVK:OXD-7 (35%):Ir-complex (15%)/TPBi (30 nm)/LiF (0.8 nm)/Al (100 nm). All samples were encapsulated inside a glove box using DELO UV cured epoxy (KATIOBOND) and capped with a 1.2 \times 1.2 cm microscope glass slide then exposed to UV light for 3 min. Current-voltage data, device efficiency, brightness and electroluminescence spectra were measured in a calibrated Labsphere LMS-100 integrating sphere. A home written NI LabVIEW programme was used to control an Agilent 6632B DC power supply, and the emission properties of the device were measured using an Ocean Optics USB4000 CCD fibre optic spectrometer. The thicknesses of the various layers in the device were measured with a J A Woolam VASE Ellipsometer using thin films which had been spin-coated on Si/SiO₂ substrates under the same conditions as the device films.

Devices with 1,3-bis(*N*-carbazolyl)benzene (mCP) host were fabricated as follows. TAPC (1,1-bis[4-[*N,N*-di(*p*-tolyl)amino]phenyl]cyclohexane), TPBi, and Tm3PyPB (1,3,5-tris(3-pyridyl-3-phenyl)benzene) were obtained from commercial sources. Indium tin oxide (ITO)-coated glass with a sheet resistance of 10 Ω per square was used as the substrate. Before device fabrication, the ITO-coated glass substrate was precleaned and exposed to UV-ozone for 15 min. PEDOT:PSS was then spin-coated onto the clean ITO substrate as a hole-injection layer. Next a mixture of complex 12 and mCP in chlorobenzene was spin-coated (10 mg mL⁻¹; 3000 rpm) to form a *ca.* 45 nm thick

emissive layer and annealed at 80 $^{\circ}$ C for 30 min to remove the residual solvent. Finally, a 5 nm-thick hole/exciton blocking layer of Tm3PyPB was vacuum deposited followed by a 30 nm-thick electron-transporting layer (ETL) of TPBi, and a cathode composed of a 1 nm-thick layer of LiF and aluminum (100 nm) was sequentially deposited through shadow masking at a pressure of 10⁻⁶ Torr. The OLED devices had a pixel size of 4 mm \times 4 mm. All measurements were performed at room temperature under ambient conditions.

Synthesis of ligands and complexes

1-(4-Mesitylpyridin-2-yl)ethanone 7. 2-Acetyl-4-chloropyridine **6**⁴⁴ (1.5 g, 9.68 mmol), 2,4,6-trimethylphenylboronic acid (1.75 g, 10.67 mmol) and PPh₃ (657 mg, 2.50 mmol) were dissolved in DME (70 mL) and the solution was degassed for 20 min by bubbling with argon. Separately, an aqueous solution of Na₂CO₃ (4.18 g, 39.43 mmol in 17 mL) was degassed. The solutions were combined and Pd(OAc)₂ (130 mg, 0.58 mmol) was added. The mixture was heated to reflux overnight under an atmosphere of argon. The solution was then cooled to RT, and the majority of the solvent was removed *in vacuo*. DCM and water were added, and the organic layer separated. The aqueous layer was extracted with additional DCM, and the extracts combined and the solvent removed *in vacuo*. The crude residue was purified by column chromatography (DCM), followed by recrystallisation from hexane to give 1-(4-mesitylpyridin-2-yl)ethanone **7** (1.2 g, 52%); m.pt. 118.9–119.9 $^{\circ}$ C; δ_H (400 MHz; CDCl₃) 8.74 (1H, dd, *J* 4.9, 0.8), 7.88 (1H, dd, *J* 1.7, 0.8), 7.31 (1H, dd, *J* 4.9, 1.7), 6.95–6.94 (2H, m), 2.79 (3H, s), 2.33 (3H, s), 1.97 (6H, s); δ_C (101 MHz; CDCl₃) 200.07, 153.73, 151.14, 149.18, 138.05, 135.64, 135.08, 128.61, 128.41, 123.06, 26.19, 21.19, 20.72; HRMS (FTMS + ESI): calcd for [C₁₆H₁₇NO + H]⁺: 240.1388. Found: 240.1388.

4-Mesityl-2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine 9. A solution of 4-mesityl-2-acetylpyridine **7** (1.20 g, 5.01 mmol) in THF (15 mL) was added dropwise to a stirred suspension of KO^tBu (0.68 g, 6.06 mmol) in dry THF solution (30 mL) which was cooled in an ice bath. After 5 min ethyl trifluoroacetate (0.65 mL, 5.51 mmol) was added slowly. The solution was allowed to stir at 0 $^{\circ}$ C for 15 min before being removed from the ice bath. The mixture was heated to reflux overnight before being cooled, and the solvent was removed under reduced pressure. Water (30 mL) was added to the resulting solid to form a suspension which was neutralised with conc. HCl. The solution was then extracted with DCM. The organic phase was dried over MgSO₄ and the solvent removed to give the presumed 1,3-dione intermediate **8** (not characterised). This was dissolved in ethanol (30 mL) and hydrazine hydrate (0.34 mL, 95%) was added. The solution was heated to reflux overnight before the solvent was removed *in vacuo*. The residue was dissolved in DCM and washed with water to remove unreacted hydrazine hydrate. The solvent was removed, and the oily residue was redissolved in ethanol and conc. HCl (0.5 mL) was added (to promote complete dehydration). The solution was heated to reflux for 5 h, before being cooled and the solvent removed. The crude solid was dissolved in DCM and washed



with water, before being dried over MgSO_4 and concentrated *in vacuo*. The crude solid was purified by column chromatography (1:3 EtOAc:DCM v/v) followed by recrystallisation from hexane to give an off-white solid, 4-mesityl-2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine **9** (277 mg, 20%); m.pt. 171.1–172.9 °C; δ_{H} (400 MHz; CDCl_3) 11.95 (1H, br s), 8.70 (1H, dd, J 5.0, 0.9), 7.47 (1H, dd, J 1.5, 0.9), 7.15 (1H, dd, J 5.0, 1.5), 6.96–7.00 (2H, m), 6.91 (1H, s), 2.35 (3H, s), 2.02 (6H, s); δ_{F} (376 MHz; CDCl_3) –62.34 (3F, s); δ_{C} (101 MHz; CDCl_3) 151.57, 149.86, 146.91, 144.42 (q, J 38.4), 143.10, 138.08, 135.43, 134.97, 128.52, 125.07, 121.40, 121.14 (q, J 267.9), 101.34, 21.06, 20.57; HRMS (FTMS + ESI): calcd for $[\text{C}_{18}\text{H}_{16}\text{N}_3\text{F}_3 + \text{H}]^+$: 332.1375. Found: 332.1379.

Iridium complex 12. $\text{IrCl}_3 \cdot 3\text{H}_2\text{O}$ (66 mg, 0.19 mmol) was added to a stirred solution of 2-(2-fluoro-4-methoxy-3-tosylphenyl)-4-mesitylpyridine **10**²⁹ (169 mg, 0.38 mmol) in 2-ethoxyethanol (5 mL). The solution was heated to 130 °C under an argon atmosphere overnight, during which time a bright yellow precipitate formed, presumed to be the dichloro bridged dimer. The solvent was removed *in vacuo* and the precipitate was redissolved in DCM/ethanol (20 mL, 3:1 v/v). 4-Mesityl-2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine **9** (77 mg, 0.28 mmol) was added and the solution was heated at 60 °C overnight under an argon atmosphere. The solution was cooled and the solvent was removed *in vacuo*. The residue was purified by column chromatography (EtOAc in DCM, 2.5% increased to 4%) to give a yellow solid, iridium complex **12** (190 mg, 70%); Anal. calc. for $\text{C}_{74}\text{H}_{65}\text{F}_5\text{IrN}_5\text{O}_6\text{S}_2$: C, 60.39; H, 4.45; N, 4.76. Found: C, 60.53; H, 4.71; N, 4.50; δ_{H} (400 MHz; CDCl_3) 8.12–8.17 (1H, m), 8.03–8.08 (1H, m), 7.89 (2H, d, J 8.2), 7.88 (2H, d, J 8.2), 7.67 (1H, d, J 5.9), 7.64 (1H, d, J 5.9), 7.59 (1H, dd, J 1.7, 0.8), 7.57 (1H, d, J 5.9), 7.27 (4H, t, J 8.7), 7.02–6.89 (8H, s), 6.78 (2H, td, J 6.1, 1.8), 5.79 (1H, s), 5.74 (1H, s), 3.47 (3H, s), 3.44 (3H, s), 2.39 (3H, s), 2.38 (3H, s), 2.34 (3H, s), 2.33 (6H, s), 2.09 (3H, s), 2.01 (3H, s), 1.98 (3H, s), 1.97 (3H, s), 1.86 (6H, s); δ_{F} (376 MHz; CDCl_3) –59.87 (3F, s), –110.50 (1F, s), –111.36 (1F, s); HRMS (FTMS + ESI): calcd for $[\text{C}_{74}\text{H}_{65}\text{N}_5\text{F}_5\text{O}_6\text{S}_2^{191}\text{Ir} + \text{H}]^+$: 1470.3981. Found: 1470.3995. Single crystals of **12**·3CH₂Cl₂ for X-ray study were grown by layering of hexane over a DCM solution of **12**; they instantly decomposed when taken out of the solvent. The X-ray experiment was carried out at $T = 120$ K on a D8 Venture (Bruker AXS) 3-circle diffractometer equipped with a $\text{I}\mu\text{S}$ Mo micro-source (Mo-K α radiation, focussing mirrors, $\lambda = 0.71073$ Å) and a PHOTON 100 CMOS area detector. The structure was solved by direct methods (SHELXS v. 2013/1 program⁶⁴) and refined by full-matrix least squares using SHELXL v. 2014/7 (ref. 65) and OLEX2⁶⁶ software. Crystal data: $\text{C}_{74}\text{H}_{67}\text{F}_5\text{IrN}_5\text{O}_6\text{S}_2 \cdot 3\text{CH}_2\text{Cl}_2$, $M = 1726.40$, triclinic, space group $P\bar{1}$ (no. 2), $a = 14.209(1)$, $b = 18.215(1)$, $c = 18.780(1)$ Å, $\alpha = 67.984(2)$, $\beta = 86.202(2)$, $\gamma = 69.653(2)^\circ$, $V = 4213.6(5)$ Å³, $Z = 2$, $D_c = 1.361$ g cm^{–3}, $\mu = 1.89$ mm^{–1}, 57 359 reflections with $2\theta \leq 50^\circ$, 14 940 unique, $R_{\text{int}} = 0.048$, $R = 0.069$ [11 521 data with $I \geq 2\sigma(I)$], $wR(F^2) = 0.201$ (all data). CCDC 1495066.† The structure contains DCM of crystallisation, of which 1.5 molecules per asymmetric unit were located and the rest (presumably dis-

ordered along infinite channels parallel to the x axis) was masked using PLATON SQUEEZE program.^{67,68} The large atomic displacement parameters, together with practical absence of Bragg diffraction at $2\theta > 50^\circ$, indicate severe internal strain, probably caused by partial solvent loss.

Iridium complex 13. $[\text{Ir}(\text{COD})\text{Cl}]_2$ (90 mg, 0.13 mmol) was added to a stirred solution of 2-(2,4-dimethoxy-3-(methylsulfonyl)phenyl)-4-mesitylpyridine **11**²⁹ (226 mg, 0.55 mmol) in 2-ethoxyethanol (5 mL). The solution was heated to 130 °C under an argon atmosphere overnight before being cooled to RT. Water was added and a yellow precipitate formed which was filtered, washed with more water and dried. The precipitate, presumed to be the intermediate dichloro bridged dimer, was dissolved in DCM/ethanol (40 mL, 3:1 v/v) and 4-mesityl-2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine **9** (90 mg, 0.27 mmol) was added and the solution was heated at 55 °C overnight under an argon atmosphere. The solution was cooled and the solvent was removed *in vacuo*. The residue was purified by column chromatography (EtOAc in DCM: gradient elution from 0% to 15%) to give a yellow solid, iridium complex **13** (98 mg, 27%); Anal. calc. for $\text{C}_{64}\text{H}_{63}\text{F}_3\text{IrN}_5\text{O}_8\text{S}_2$: C, 57.21; H, 4.73; N, 5.21. Found: C, 57.17; H, 5.07; N, 4.68; δ_{H} (400 MHz; CD_2Cl_2) 8.47 (1H, d, J 1.4), 8.38 (1H, d, J 1.4), 7.80–7.74 (3H, m), 7.65 (1H, dd, J 1.8, 0.8), 6.98 (5H, s), 6.95 (2H, s), 6.91 (1H, dd, J 5.7, 1.8), 6.84 (1H, dd, J 5.9, 1.9), 6.81 (1H, dd, J 5.9, 1.9), 6.03 (1H, s), 6.01 (1H, s), 3.88 (3H, s), 3.85 (3H, s), 3.61 (3H, s), 3.60 (3H, s), 3.22 (3H, s), 3.19 (3H, s), 2.33 (3H, s), 2.32 (3H, s), 2.31 (3H, s), 2.09 (3H, s), 2.06 (3H, s), 2.05 (3H, s), 2.01 (3H, s), 1.88 (3H, s), 1.85 (3H, s); δ_{F} (376 MHz; CDCl_3) –58.48 (s); HRMS (FTMS + ESI): calcd for $[\text{C}_{64}\text{H}_{63}\text{F}_3\text{N}_5\text{O}_8\text{S}_2^{191}\text{Ir} + \text{H}]^+$: 1342.3754. Found: 1342.3802.

2-(3-(Trifluoromethyl)-1H-pyrazol-5-yl)pyridine 16. 2-Acetylpyridine (1.00 g, 8.25 mmol) and ethyltrifluoroacetate (2.35 g, 16.51 mmol) were added dropwise simultaneously to a stirred suspension of NaH (396 mg, 16.51 mmol) in THF (20 mL, dry) with caution (gas evolution). The mixture was stirred at RT for 30 min before being heated to reflux overnight. The reaction was cooled and quenched with water. The reaction mixture was acidified to pH 6 with dilute HCl (2 M) and then extracted with EtOAc (3×60 mL). The organic phases were combined, dried over MgSO_4 , filtered and the solvent was removed *in vacuo* to give the crude 1,3-dione. The dione was dissolved in ethanol (20 mL) and $\text{N}_2\text{H}_4 \cdot \text{H}_2\text{O}$ (4 mL) was added. The solution was heated to reflux overnight before being cooled to RT. The solvent was removed *in vacuo* and the residue was purified by column chromatography (hexane:EtOAc 3:2 v/v) to give an off-white solid, 2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine **16** (1.31 g, 75%); δ_{H} (400 MHz; CDCl_3) 11.74 (1H, s), 8.65 (1H, ddd, J 4.9, 1.8, 1.0), 7.82 (1H, td, J 7.8, 1.7), 7.65 (1H, dt, J 7.9, 1.1), 7.33 (1H, ddd, J 7.6, 4.9, 1.1), 6.96 (1H, s); δ_{F} (376 MHz; CDCl_3) –62.35 (s).

Iridium complex 14. 2-(2-Fluoro-4-methoxy-3-tosylphenyl)-4-mesitylpyridine **10**²⁹ (110 mg, 0.23 mmol) and $\text{IrCl}_3 \cdot 3\text{H}_2\text{O}$ (37 mg, 0.10 mmol) were combined in 2-ethoxyethanol (5 mL), and the mixture was heated to reflux overnight under a nitrogen atmosphere. The reaction was cooled to RT, and the



solvent removed *in vacuo*. The residue was redissolved in DCM/EtOH (3 : 1 v/v, 20 mL) and 2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine **16** (28 mg, 0.13 mmol) and Na₂CO₃ (11 mg, 0.10 mmol) were added. The solution was heated to 55 °C for 6 h, before being cooled to RT and the solvent removed *in vacuo*. The residue was purified by column chromatography (0–3% EtOAc in DCM) to give the product as a yellow solid, iridium complex **14** (109 mg, 77%); Anal. calc. for C₆₅H₅₅F₅IrN₅O₆S₂: C, 57.68; H, 4.10; N, 5.17. Found: C, 57.84; H, 4.33; N, 4.92; δ_{H} (400 MHz, CDCl₃) 8.11 (1H, s), 8.05 (1H, s), 7.95–7.78 (6H, m), 7.70–7.64 (1H, m), 7.56 (1H, d, *J* 6.0), 7.50–7.43 (2H, m), 7.29 (1H, d, *J* 0.8), 7.26–7.22 (2H, m), 7.18–7.11 (1H, m), 7.01 (1H, s), 6.93 (4H, d, *J* 6.4), 6.77 (1H, dd, *J* 5.9, 1.8), 6.71 (1H, dd, *J* 6.0, 1.8), 5.72 (1H, s), 5.70 (1H, s), 3.44 (3H, s), 3.41 (3H, s), 2.39 (3H, s), 2.38 (3H, s), 2.33 (6H, s), 1.99 (3H, s), 1.97 (6H, s), 1.93 (3H, s); δ_{F} (376 MHz; CDCl₃) –59.85 (3F, s), –110.73 (1F, s); –111.48 (1F, s); HRMS (FTMS + ESI): calcd for [C₆₅H₅₅N₅O₆F₅S₂¹⁹¹Ir + H]⁺: 1352.3198. Found: 1352.3193.

Iridium complex 15. 2-(2,4-Dimethoxy-3-(methylsulfonyl)phenyl)-4-mesitylpyridine **11**²⁹ (198 mg, 0.48 mmol) and [Ir(COD)Cl]₂ (79 mg, 0.12 mmol) were combined in 2-ethoxyethanol (5 mL), and the mixture was heated to reflux overnight under a nitrogen atmosphere. The reaction was cooled to RT, and the solvent removed *in vacuo*. The residue was redissolved in DCM/EtOH (3 : 1 v/v, 20 mL) and 2-(3-(trifluoromethyl)-1H-pyrazol-5-yl)pyridine **16** (63 mg, 0.30 mmol) and Na₂CO₃ (50 mg, 0.47 mmol) were added. The solution was heated to 55 °C for 5 h, before being cooled to RT and the solvent removed *in vacuo*. The residue was purified by column chromatography (0–10% EtOAc in DCM) to give the product as a yellow solid, iridium complex **15** (28 mg, 56%); Anal. calc. for C₅₅H₅₃F₃IrN₅O₈S₂: C, 53.91; H, 4.36; N, 5.72. Found: C, 53.48; H, 4.43; N, 5.55; δ_{H} (400 MHz, CDCl₃) 8.46 (1H, d, *J* 1.8), 8.40 (1H, d, *J* 1.8), 7.88 (2H, m), 7.82 (1H, d, *J* 5.9), 7.75 (1H, d, *J* 5.6), 7.52 (1H, d, *J* 5.9), 7.16 (1H, td, *J* 6.0, 2.6), 7.04 (1H, s), 6.98 (2H, s), 6.96 (2H, s), 6.85 (1H, dd, *J* 5.9, 1.9), 6.72 (1H, dd, *J* 5.9, 1.9), 5.96 (1H, s), 5.89 (1H, s), 3.91 (3H, s), 3.91 (3H, s), 3.60 (3H, s), 3.58 (3H, s), 3.30 (3H, s), 3.27 (3H, s), 2.35 (6H, s), 2.03 (6H, s), 2.01 (3H, s), 1.97 (3H, s); δ_{F} (376 MHz; CDCl₃) –60.00 (s); HRMS (FTMS + ESI): calcd for [C₅₅H₅₃N₅O₈F₃S₂¹⁹¹Ir + H]⁺: 1224.2972. Found: 1224.2987.

Acknowledgements

We thank EPSRC grant EL/L02621X/1 for funding the work in Durham.

References

- V. W.-W. Yam and K. M.-C. Wong, *Chem. Commun.*, 2011, 47, 11579.
- M. A. Baldo, D. F. O'Brien, Y. You, A. Shoustikov, S. Sibley, M. E. Thompson and S. R. Forrest, *Nature*, 1998, **395**, 151.
- H. Yersin, *Highly Efficient OLEDs with Phosphorescent Materials*, Wiley-VCH, Darmstadt, 2008.
- M. S. Lowry and S. Bernhard, *Chem. – Eur. J.*, 2006, **12**, 7970.
- K. K.-W. Lo, W.-K. Hui, C.-K. Chung, K. H.-K. Tsang, D. C.-M. Ng, N. Zhu and K.-K. Cheung, *Coord. Chem. Rev.*, 2005, **249**, 1434.
- K. Müllen and U. Scherf, *Organic Light Emitting Devices: Synthesis, Properties and Applications*, Wiley-VCH Verlag GmbH & Co. KGaA, 2006.
- R. Mertens, *The OLED Handbook. A Guide to OLED Technology, Industry and Market*, 2014: <http://www.oled-info.com/handbook>.
- Z.-R. Li and H. Meng, *Organic Light-Emitting Materials and Devices*, CRC Press, Boca Raton, Florida, 2006.
- M. Du, Y. Feng, D. Zhu, T. Peng, Y. Liu, Y. Wang and M. R. Bryce, *Adv. Mater.*, 2016, **28**, 5963.
- L. Ying, C.-L. Ho, H. Wu, Y. Cao and W.-Y. Wong, *Adv. Mater.*, 2014, **26**, 2459.
- E. Holder, B. M. W. Langeveld and U. S. Schubert, *Adv. Mater.*, 2005, **17**, 1109.
- P. T. Chou and Y. Chi, *Chem. – Eur. J.*, 2007, **13**, 380.
- X. Yang, G. Zhou and W.-Y. Wong, *Chem. Soc. Rev.*, 2015, **44**, 8484.
- Y. You and S. Y. Park, *Dalton Trans.*, 2009, 1267.
- S. Ladouceur and E. Zysman-Colman, *Eur. J. Inorg. Chem.*, 2013, 2985.
- E. Baranoff and B. F. Curchod, *Dalton Trans.*, 2015, **44**, 8318.
- S. H. Kim, J. Jang, S. J. Lee and J. Y. Lee, *Thin Solid Films*, 2008, **517**, 722.
- S. Lamansky, P. Djurovich, D. Murphy, F. Abdel-Razzaq, R. Kwong, I. Tsyba, M. Bortz, B. Mui, R. Bau and M. E. Thompson, *Inorg. Chem.*, 2001, **40**, 1704.
- T. Sajoto, P. I. Djurovich, A. Tamayo, M. Yousufuddin, R. Bau, M. E. Thompson, R. J. Holmes and S. R. Forrest, *Inorg. Chem.*, 2005, **44**, 7992.
- C. Fan, Y. Li, C. Yang, H. Wu, J. Qin and Y. Cao, *Chem. Mater.*, 2012, **24**, 4581.
- J. B. Kim, S. H. Han, K. Yang, S. K. Kwon, J. J. Kim and Y. H. Kim, *Chem. Commun.*, 2015, **51**, 58.
- S. Lee, S. O. Kim, H. Shin, H. J. Yun, K. Yang, S. K. Kwon, J. J. Kim and Y. H. Kim, *J. Am. Chem. Soc.*, 2013, **135**, 14321.
- L.-L. Wu, C.-H. Yang, I. W. Sun, S.-Y. Chu, P.-C. Kao and H.-H. Huang, *Organometallics*, 2007, **26**, 2017.
- H. Oh, K.-M. Park, H. Hwang, S. Oh, J. H. Lee, J.-S. Lu, S. Wang and Y. Kang, *Organometallics*, 2013, **32**, 6427.
- E. Orselli, G. S. Kottas, A. E. Konradsson, P. Coppo, R. Frohlich, L. de Cola, A. van Dijken, M. Buchel and H. Borner, *Inorg. Chem.*, 2007, **46**, 11082.
- J. Li, P. I. Djurovich, B. D. Alleyne, M. Yousufuddin, N. N. Ho, J. C. Thomas, J. C. Peters, R. Bau and M. E. Thompson, *Inorg. Chem.*, 2005, **44**, 1713.
- J. Li, P. I. Djurovich, B. D. Alleyne, I. Tsyba, N. N. Ho, R. Bau and M. E. Thompson, *Polyhedron*, 2004, **23**, 419.



- 28 H.-J. Seo, K.-M. Yoo, M. Song, J. S. Park, S.-H. Jin, Y. I. Kim and J.-J. Kim, *Org. Electron.*, 2010, **11**, 564.
- 29 H. Benjamin, Y. Zheng, A. S. Batsanov, M. A. Fox, H. A. Al-Attar, A. P. Monkman and M. R. Bryce, *Inorg. Chem.*, 2016, **55**, 8612.
- 30 C.-H. Yang, M. Mauro, F. Polo, S. Watanabe, I. Muenster, R. Fröhlich and L. De Cola, *Chem. Mater.*, 2012, **24**, 3684.
- 31 C. H. Hsieh, F. I. Wu, C. H. Fan, M. J. Huang, K. Y. Lu, P. Y. Chou, Y. H. Yang, S. H. Wu, I. C. Chen, S. H. Chou, K. T. Wong and C. H. Cheng, *Chem. – Eur. J.*, 2011, **17**, 9180.
- 32 H. Fu, Y.-M. Cheng, P.-T. Chou and Y. Chi, *Mater. Today*, 2011, **14**, 472.
- 33 L. Shi, B. Hong, W. Guan, Z. Wu and Z. Su, *J. Phys. Chem. A*, 2010, **114**, 6559.
- 34 J. M. Fernandez-Hernandez, J. I. Beltran, V. Lemaure, M. D. Galvez-Lopez, C. H. Chien, F. Polo, E. Orselli, R. Frohlich, J. Cornil and L. De Cola, *Inorg. Chem.*, 2013, **52**, 1812.
- 35 C.-H. Chang, C.-C. Chen, C.-C. Wu, C.-H. Yang and Y. Chi, *Org. Electron.*, 2009, **10**, 1364.
- 36 J. Frey, B. F. E. Curchod, R. Scopelliti, I. Tavernelli, U. Rothlisberger, M. K. Nazerruddin and E. Baranoff, *Dalton Trans.*, 2014, **43**, 5667.
- 37 V. N. Kozhevnikov, K. Dahms and M. R. Bryce, *J. Org. Chem.*, 2011, **76**, 5143.
- 38 S. Schmidbauer, A. Hohenleutner and B. Konig, *Adv. Mater.*, 2013, **25**, 2114.
- 39 V. N. Kozhevnikov, Y. Zheng, M. Clough, H. A. Al-Attar, G. C. Griffiths, K. Abdullah, S. Raisys, V. Jankus, M. R. Bryce and A. P. Monkman, *Chem. Mater.*, 2013, **25**, 2352.
- 40 A. F. Henwood, A. K. Bansal, D. B. Cordes, A. M. Z. Slawin, I. D. W. Samuel and E. Zysman-Colman, *J. Mater. Chem. C*, 2016, **4**, 3726.
- 41 (a) D. Rota Martir, A. K. Bansal, V. Di Mascio, D. B. Cordes, A. F. Henwood, A. M. Z. Slawin, P. C. J. Kamer, L. Martinez-Sarti, A. Pertegas, H. J. Bolink, I. D. W. Samuel and E. Zysman-Colman, *Inorg. Chem. Front.*, 2016, **3**, 218; (b) D. Rota Martir, G. J. Hedley, D. B. Cordes, A. M. Z. Slawin, D. Escudero, D. Jacquemin, T. Kosikova, D. Philip, D. M. Dawson, S. E. Ashbrook, I. D. W. Samuel and E. Zysman-Colman, *Dalton Trans.*, 2016, **45**, 17195; (c) D. Rota Martir, C. Momblona, A. Pertegas, D. B. Cordes, A. M. Z. Slawin, H. J. Bolink and E. Zysman-Colman, *ACS Appl. Mater. Interfaces*, 2016, **8**, 33907.
- 42 J. Li, Q. Zhang, H. He, L. Wang and J. Zhang, *Dalton Trans.*, 2015, **44**, 8577.
- 43 E. Bisagni, M. Rautureau and C. Huel, *Heterocycles*, 1989, **29**, 1815.
- 44 E. Busto, V. Gotor-Fernández and V. Gotor, *Tetrahedron: Asymmetry*, 2006, **17**, 1007.
- 45 C.-C. Cheng, W.-S. Yu, P.-T. Chou, S.-M. Peng, G.-H. Lee, P.-C. Wu, Y.-H. Song and Y. Chi, *Chem. Commun.*, 2003, 2628.
- 46 C.-H. Lin, Y.-C. Chiu, Y. Chi, Y.-T. Tao, L.-S. Liao, M.-R. Tseng and G.-H. Lee, *Organometallics*, 2012, **31**, 4349.
- 47 M. Nonoyama, *Bull. Chem. Soc. Jpn.*, 1974, **47**, 767.
- 48 C. Adachi, R. C. Kwong, P. Djurovich, V. Adamovich, M. A. Baldo, M. E. Thompson and S. R. Forrest, *Appl. Phys. Lett.*, 2001, **79**, 2082.
- 49 P. J. Hay, *J. Phys. Chem. A*, 2002, **106**, 1634.
- 50 N. G. Connelly and W. E. Geiger, *Chem. Rev.*, 1996, **96**, 877.
- 51 D. Tordera, J. J. Serrano-Pérez, A. Pertegás, E. Ortí, H. J. Bolink, E. Baranoff, M. K. Nazeeruddin and J. Frey, *Chem. Mater.*, 2013, **25**, 3391.
- 52 V. Sivasubramaniam, F. Brodkorb, S. Hanning, H. P. Loeb, V. van Elsbergen, H. Boerner, U. Scherf and M. Kreyenschmidt, *J. Fluorine Chem.*, 2009, **130**, 640.
- 53 V. Sivasubramaniam, F. Brodkorb, S. Hanning, H. Loeb, V. Elsbergen, H. Boerner, U. Scherf and M. Kreyenschmidt, *Cent. Eur. J. Chem.*, 2009, **7**, 836.
- 54 R. Seifert, I. Rabelo de Moraes, S. Scholz, M. C. Gather, B. Lüssem and K. Leo, *Org. Electron.*, 2013, **14**, 115.
- 55 J.-H. Jou, W.-B. Wang, S.-M. Shen, S. Kumar, I. M. Lai, J.-J. Shyue, S. Lengvinaite, R. Zostautiene, J. V. Grazulevicius, S. Grigalevicius, S.-Z. Chen and C.-C. Wu, *J. Mater. Chem.*, 2011, **21**, 9546.
- 56 S.-J. Su, Y. Takahashi, T. Chiba, T. Takeda and J. Kido, *Adv. Funct. Mater.*, 2009, **19**, 1260.
- 57 D. Sun, H. Zhou, H. Li, X. Sun, Y. Zheng, Z. Ren, D. Ma, M. R. Bryce and S. Yan, *J. Mater. Chem. C*, 2014, **2**, 8277.
- 58 M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, B. Mennucci, G. A. Petersson, H. Nakatsuji, M. Caricato, X. Li, H. P. Hratchian, A. F. Izmaylov, J. Bloino, G. Zheng, J. L. Sonnenberg, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, J. A. Montgomery Jr., J. E. Peralta, F. Ogliaro, M. Bearpark, J. J. Heyd, E. Brothers, K. N. Kudin, V. N. Staroverov, R. Kobayashi, J. Normand, K. Raghavachari, A. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, N. Rega, J. M. Millam, M. Klene, J. E. Knox, J. B. Cross, V. Bakken, C. Adamo, J. Jaramillo, R. Gomperts, R. E. Stratmann, O. Yazyev, A. J. Austin, R. Cammi, C. Pomelli, J. W. Ochterski, R. L. Martin, K. Morokuma, V. G. Zakrzewski, G. A. Voth, P. Salvador, J. J. Dannenberg, S. Dapprich, A. D. Daniels, O. Farkas, J. B. Foresman, J. V. Ortiz, J. Cioslowski and D. J. Fox, *Gaussian 09, Revision A.02*, Gaussian, Inc., Wallingford CT, 2009.
- 59 (a) A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648; (b) C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B: Condens. Matter*, 1988, **37**, 785.
- 60 (a) T. H. Dunning Jr. and P. J. Hay, *Modern Theoretical Chemistry*, ed. H. F. Schaefer III, Plenum, New York, 1976, vol. 3; (b) P. J. Hay and W. R. Wadt, *J. Chem. Phys.*, 1985, **82**, 270; (c) W. R. Wadt and P. J. Hay, *J. Chem. Phys.*, 1985, **82**, 284; (d) P. J. Hay and W. R. Wadt, *J. Chem. Phys.*, 1985, **82**, 299.



- 61 (a) G. A. Petersson and M. A. Al-Laham, *J. Chem. Phys.*, 1991, **94**, 6081; (b) G. A. Petersson, A. Bennett, T. G. Tensfeldt, M. A. Al-Laham, W. A. Shirley and J. Mantzaris, *J. Chem. Phys.*, 1988, **89**, 2193.
- 62 A. R. Allouche, *J. Comput. Chem.*, 2011, **32**, 174.
- 63 N. M. O'Boyle, A. L. Tenderholt and K. M. Langner, *J. Comput. Chem.*, 2008, **29**, 839.
- 64 G. Sheldrick, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 2008, **64**, 112.
- 65 G. Sheldrick, *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.*, 2015, **71**, 3.
- 66 L. J. Bourhis, O. V. Dolomanov, R. J. Gildea, J. A. K. Howard and H. Puschmann, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 2015, **71**, 59.
- 67 A. Spek, *Acta Crystallogr., Sect. D: Biol. Crystallogr.*, 2009, **65**, 148.
- 68 P. van der Sluis and A. L. Spek, *Acta Crystallogr., Sect. A: Fundam. Crystallogr.*, 1990, **46**, 194.

