

Nonconjugated Polyurethane Derivatives with Aggregation-Induced Luminochromism for Multicolor and White Photoluminescent Films

Nan Jiang, Ya-Jie Meng, Chang-Yi Zhu, Ke-Xin Li, Xin Li, Yan-Hong Xu,* Jia-Wei Xu,* and Martin R. Bryce*



Cite This: *ACS Macro Lett.* 2024, 13, 1226–1232



Read Online

ACCESS |




Metrics & More



Article Recommendations



Supporting Information

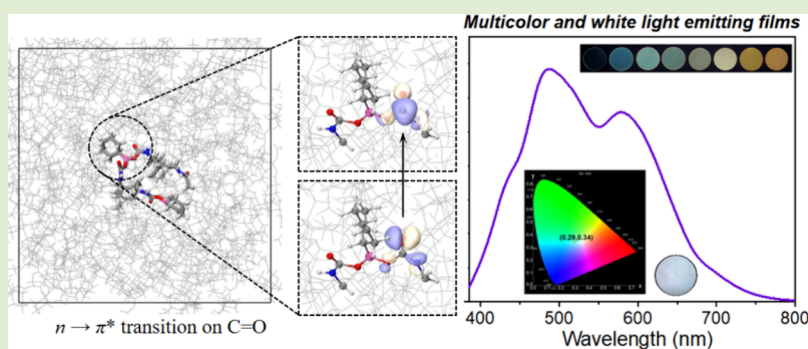

ABSTRACT: A simple and effective strategy to obtain solid-state multicolor emitting materials is a particularly attractive topic. Nonconventional/nonconjugated polymers are receiving widespread attention because of their advantages of rich structural diversity, low cost, and good processability. However, it is difficult to control the molecular conformation or to obtain the crystal structure of amorphous molecules, which means it is a challenge to obtain nontraditional polymeric materials with multicolor emission. In this work, a polyurethane derivative (PUH) with red-shifted emission was synthesized by a simple one-pot polymerization reaction. By exploiting the aggregation-induced luminochromism of PUH, a series of plastic films with tunable emission from blue to orange, and white-light emission, was obtained by doping different amounts of PUH into poly(methyl methacrylate) (PMMA), thereby changing the aggregation degree of PUH. This work demonstrates the excellent promise of polyurethane derivatives for the simple fabrication of large-scale flexible luminescent films.

Traditional photoluminescence relies on the excitation of the delocalized electrons within aromatic or extended π -systems.^{1,2} However, these discrete chromophores often face the dilemma of concentration-dependent emission quenching, resulting in a significant reduction in the emission intensity of solid/aggregated samples, which greatly limits their photoluminescent applications.^{3–7} Since the 1970s, the emergence of nonconventional luminescent materials has overcome this problem.^{8–11} It has been found that some organic small molecules, macromolecules, inorganic, and organic/inorganic hybrid materials without traditional fluorophores also exhibit inexplicable and nonconventional intrinsic luminescence properties.^{12–14} Unlike traditional chromophores, nonconventional chromophores do not require (hetero)aromatic π -conjugated structures, and they work via the collective intra- and intermolecular associations and the subsequent through-space electronic conjugation of nonconjugated subunits to achieve emission.

These so-called nonconventional chromophores comprise hydroxyl (–OH), sulfur (–S–), ester (–COOR), carboxyl

(–COOH), carbonyl (C=O), alkene (C=C), ether (–O–), and amide (–NHCO–) units and others.^{15,16} However, due to the lack of large π -conjugated units, these nonconventional luminescence are mostly limited to blue emission regions. Enhancing the through-space electronic communication and conjugation of materials by polymerization has been recognized as an effective strategy for regulating nontraditional luminescence.^{17–20} Nonconventional luminescent polymers (NCLPs) have emerging applications in anticounterfeiting, sensor and photoelectric devices, clinical therapy, and other fields.^{21–23}

Received: August 8, 2024

Revised: September 2, 2024

Accepted: September 4, 2024

The optimal molecular design principles of NCLPs with longer wavelength emission are still being explored.^{24–28} Strong and stable interchain and/or intrachain through-space interactions (TSIs) are ways to facilitate strong, red-shifted emission.²⁹ Effective TSIs require an appropriate balance of the rigidity and flexibility of the polymer chains. For example, Zhang et al. used different anhydrides to manipulate segmental flexibility and rigidity of nonconjugated and nonaromatic polyesters, and obtained variable (yellow-green) luminescence.³⁰ Wang et al. synthesized poly(itaconic anhydride-co-vinyl caprolactam) with orange–red emission, emphasizing that a suitable molecular chain conformation is conducive to stronger intrachain and/or interchain interactions as the decisive factor in determining the emission of these NCLPs.³¹ Nonaromatic poly(maleimides) provide controllable blue-to-red emission.³² These outstanding examples are precedents for tuning the long-wavelength emission of unconventional materials. However, monotonic luminescence modulation usually does not meet practical application requirements. Nonconventional chromophores with adjustable multicolor luminescence have also been studied. For instance, Cloutet et al. established the importance of oxygen aggregation (caused by the restricted polymer conformation) for the multichromatic photoluminescence of poly(dihydropyran).³³

Inspired by the above background, we have now synthesized a nonconjugated polyurethane derivative with an unsealed end structure using cyclohexylboronic acid and isophorone diisocyanate monomers. The cyclohexyl and isophorone rings bring greater rigidity to the polyurethane skeleton as opposed to flexible linear alkyl chain monomers. Polyurethane is an organic polymer intermediate between plastics and rubber.³⁴ Because of its favorable mechanical properties, excellent resistance to climate, chemical corrosion, fatigue, wear, and high impact resistance, it has become one of the most commonly used polymers in everyday life and in industry.^{35–37} However, research on polyurethane derivatives as luminescent materials is often ignored. The repeating urethane unit [–NHC(O)O–] is an ideal multiheteroatomic template for exploring nontraditional luminescence phenomena with excellent application potentials.^{38–41}

This work describes a luminescent polyurethane derivative (PUH) with long-wavelength emission, which is the result of the appropriate rigid, distorted molecular structure and electron-rich repeat units. In addition, using the luminescence characteristics of PUH, a series of films with a fluorescent gradient were prepared by adjusting the doping ratio of PUH and poly(methyl methacrylate) (PMMA) to regulate the extent of aggregation of the polymer, finally, to obtain transparent plastic films with multicolor (blue to orange) and white luminescence. This work provides experimental and theoretical validation for the design strategy of long-wavelength emitting NCLPs and serves as a new case study for their potential practical applications.

Through simple one-pot polymerization reactions, multicolor fluorescent polyurethane derivatives were obtained (Figure 1a, Tables S1 and S2), named P1, P2, P3, PUC, and PUH (Figures S1 and S2). ¹H NMR and FT-IR spectra (Figures S3–S9) show that the PUs are well-structured materials. The absorption and emission spectra showed that the PUs exhibited different light utilization and a blue to orange-red luminescence, respectively, under 365 nm ultra-violet excitation (Figures 1b and S10). Since the PUs' structure does not contain any conventional chromophore, their

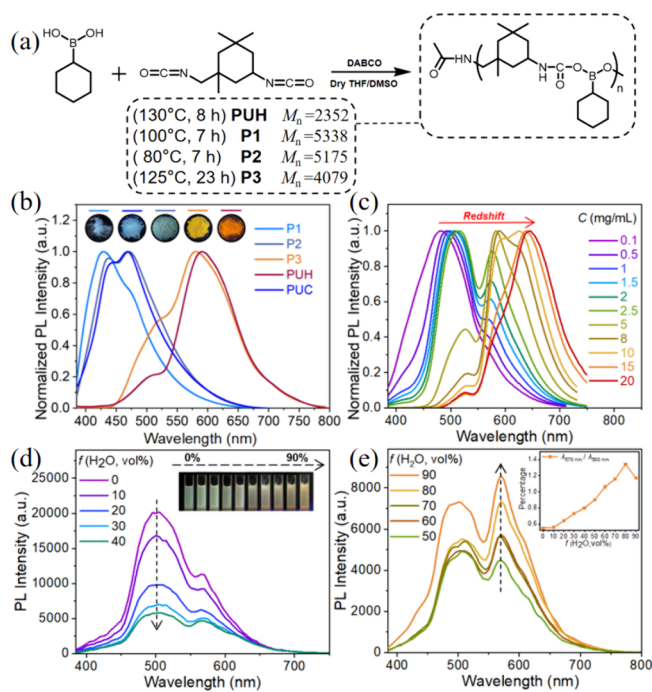


Figure 1. (a) Synthetic method and chemical structures of PUH, P1, P2, and P3, and the corresponding average molecular weights. (b) Normalized emission spectra of P1, P2, P3, PUH, and PUC powder ($\lambda_{\text{ex}} = 365$ nm). Insets: the corresponding fluorescence photographs under 365 nm UV illumination. (c) Normalized emission spectra of PUH/DMSO with different concentrations. (d, e) Emission spectra of PUH (1 mg mL⁻¹) in DMSO–water mixtures with different water fractions (0–90% v/v) at room temperature. Insets: corresponding photographs under 365 nm UV illumination, and the intensity ratio plot of $\lambda_{570\text{ nm}}/\lambda_{500\text{ nm}}$ with the increase of water content.

luminescence is ascribed to polymerization-induced non-conventional intrinsic luminescence.

Taking PUH which has the reddest emission as the main focus, the emission spectra of PUH/DMSO solutions at different concentrations revealed a large redshift of 164 nm for the main peak with the gradual increase of concentration from 0.1 to 20 mg mL⁻¹, with aggregation behavior of PUH causing the changes from green to orange emission (Figure 1c). Such wide variations in emission peaks as observed here with PUH are rare,^{3,42,43} which suggests its potential for multifunctional applications. Steady-state fluorescence spectra in different solvents showed that there is charge transfer from electron donor to electron acceptor (Figure S11) in the PUH system, which is conducive to its luminescence.^{44–46}

The aggregation process of PUH was probed by scanning electron microscopy (SEM). Initially, the cyclohexylboronic acid monomer has a sparse irregular structure; however, after polymerization, at the same magnification, PUH presents a very aggregated nanospherical structure (Figure S12). It can be inferred that this progressive aggregation behavior caused by polymerization is closely related to the change in the materials' photophysical properties. As shown in Figures 2 and S13, the microstructure of the PUH solutions was monitored at different concentrations via SEM and dynamic light scattering (DLS). Even at low concentrations, PUH showed a relatively concentrated structure compared to that of the monomer, except with a smaller particle size (Figure 2a). As the concentration of the solution increased, PUH gradually accumulated and slowly transformed into a large nanosized

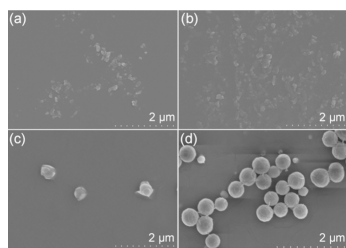


Figure 2. SEM images of PUH: (a) 0.1 mg mL⁻¹, (b) 1 mg mL⁻¹, (c) 5 mg mL⁻¹, and (d) 10 mg mL⁻¹ in pure DMSO solution.

spherical aggregate structure (Figures 2b–d and S13). This change in the microscopic structure correlates positively with the concentration-dependent emission data in Figure 1c.

The emission spectra of solid powders of PUs at different excitation wavelengths are presented in Figures S14 and S15. PUH and P3 with longer wavelengths of emission have weaker excitation-dependent emission characteristics. The SEM results showed that P3 had a compact microscopic aggregation structure (Figure S16) similar to that of PUH (Figure 2). It is assumed that the high reaction temperature increases the molecular aggregation. The microstructures of P1 and P2 are relatively loose. It is speculated that compact aggregation is not only beneficial to obtain long wavelength emission, but also to obtain luminous clusters with uniform electronic delocalization.

1,4-Cyclohexanediol monomer was selected for comparative experiments. Even if the reaction temperature and time were increased to 140 °C and 21 h, product PUC still showed only blue fluorescence. Therefore, the importance of the boron atom in the long-wavelength emission in this system is confirmed. This will be discussed in detail in the theoretical calculations section.

Obvious aggregation-induced luminous discoloration was also observed in the mixed DMSO/water solutions of PUH (Figure 1d,e). When PUH is dissolved in the good solvent DMSO, due to the low concentration (0.1 mg mL⁻¹) the PUH molecules are in a sparsely dispersed state. The emission spectrum of the pure PUH solution has a main peak at 500 nm and a shoulder peak at 570 nm (Figure 1d) showing green emission under 365 nm UV light. However, with the gradual addition of adverse solvent water, the dispersed PUH molecules randomly rearrange and passively aggregate.^{14,47,48} The sparse molecular chains gradually aggregate into larger luminescent clusters. Thus, the emission intensity at short-wavelength (500 nm) gradually decreases, while the proportion of long-wavelength emission (570 nm) gradually increases, and the luminous color of the mixed solution gradually becomes yellow, similar to its emission in the solid state.

Unlike traditional flat luminous dyes, which rely on the formation of excimers to produce multiplex emission, polymers with nonconjugated structures often rely on soft and variable inter/intrachain entanglements to produce a variety of aggregate emission species of different sizes. These aggregates have heterogeneous electron delocalization, and thus they exhibit multiplex emissions.^{49–51} However, such multimodal emission usually has a narrow range of variation. PUH in the aggregated state exhibits a ratio-type multiplex emission with a large gamut variation.^{32,52} To eliminate the effect of a small amount of impurities that may exist, we mixed the cyclohexyl boronic acid monomer with PUH (1:1 w/w) and added the good solvent DMSO to make a solution, and

then gradually added the poor solvent (water). As shown in Figure S17, the mixed solution did not produce the chromic behavior seen in Figure 1. The results suggest that the chromic behavior is derived from the self-chain aggregation of PUH, rather than possible impurities from the monomer. In addition, the short-wavelength emission of P1 and P2 (Figure 1a), which have the same chemical structure as PUH but different molecular weights and aggregation structures, should rule out the possibility that the polychromatic emission behavior of PUH is caused by the byproducts of the polymerization reaction.

Hybrid quantum mechanics/molecular mechanics (QM/MM) simulations suggested that the excitation feature for the S₁ state of PUH shows an *n* → π^* transition on C=O, as revealed by natural transition orbitals (Figure 3a). To

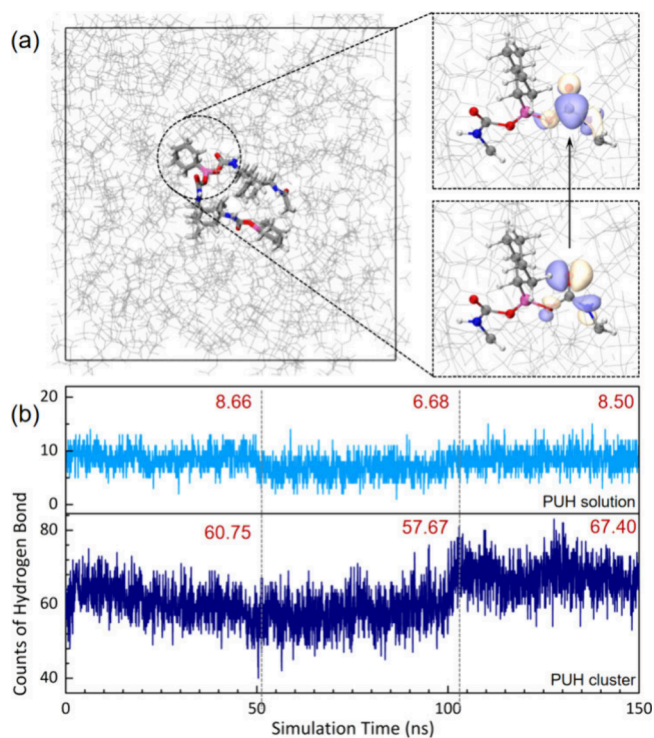


Figure 3. (a) Natural transition orbitals obtained from QM/MM simulations based on a snapshot taken from the MD3 trajectory. (b) Counts of hydrogen bonds during the three-stage MD simulation of PUH in aqueous solution (upper) and aggregate cluster environment (lower).

understand the luminescence mechanism of PUH, three-stage molecular dynamics (MD) simulations, including (1) 50.0 ns equilibrium at 300 K, (2) 50.0 ns heating at synthetic temperature, and (3) 50.0 ns annealing to 300 K, were performed for PUH in both aqueous and aggregate environments. As shown in Figure 3b, in aqueous solution, the number of hydrogen bonds was not affected by the annealing process; the average number changed by only 0.16 (8.66 → 8.50). These hydrogen bonds were all formed between PUH and water and therefore were not sensitive to annealing, while intramolecular hydrogen bonding was almost not detected. In contrast, in the aggregate environment, the number of intermolecular hydrogen bonds showed a significant increase (60.75 → 67.40) after annealing, indicating that conformational change at a higher synthetic temperature achieved an

enhanced cluster structure and contributed to the red-shift in luminescence. These results are consistent with the experimental data (Figure 1a).

To further elucidate the role of the matrix environment in influencing the luminescence wavelength, the excited states of PUH in the gas phase, aqueous solution and aggregate environment were calculated for comparison [PUH, PUH(aq) and PUH(s), respectively]. As summarized in Table S3, the excitation energy of the S_1 state was slightly decreased by aqueous solution, from 6.996 to 6.978 eV, both of which are too high to respond to common UV–vis excitation and are also unable to show luminescence within the visible region. This demonstrates that hydrogen bonds formed between PUH and solvent molecules are not the major factor for red-shifting the emission. However, the aggregate environment brought a significant decrease, reaching a low-lying S_1 state with an excitation energy of only 4.609 eV excitation energy. Such an energy gap is suitable for high-efficient UV–vis excitation and visible luminescence. We can, therefore, conclude that hydrogen bonding, along with other intermolecular non-covalent interactions formed in the aggregate environment, play a significant role in assisting the generation of luminescence and increasing the emission wavelength. The n orbital in aggregated PUH is much higher than that in the gas phase or aqueous solution and gives the smallest $n-\pi^*$ gap among the three systems, which corresponds well to the statistical number of hydrogen bonds (Table S4 and Figure 3b).

As presented by natural transition orbitals (NTOs) with eigenvalue $>10^{-6}$ in Figures S18–S20, simply replacing the boron atom by a carbon–hydrogen or a nitrogen atom does not change the excitation feature of the PUH's photofunctional center, i.e., the S_1 state with the $n \rightarrow \pi^*$ property is retained. Although the NTOs show that luminescence of PUH originates from the $n \rightarrow \pi^*$ transition on C=O, where the boron atom is not directly involved, by replacing boron with carbon (PUH-C) and nitrogen (PUH-N), the excitation energy of the S_1 state still shows a difference and PUH has the most stable S_1 state (Table S3). From PUH-N, PUH-C to PUH, a higher n orbital level leads to a smaller $n-\pi^*$ energy gap, giving a more stable S_1 excited state, observed as a red-shift in the emission wavelength in the aggregated state (Table S4). By comparison, with B atoms as the electron-deficient center, reducing the electron density of the n orbital nearby C=O through a field effect, increases the energy of the n orbital, reducing the energy level difference of $n-\pi^*$, finally reducing the S_1 energy level of PUH, especially in the aggregation state (Figure 4).

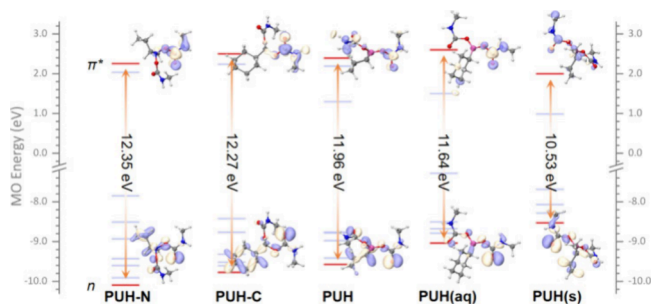


Figure 4. Energy level diagram of PUH-N, PUH-C, PUH, PUH(aq), and PUH(s).

To explore a practical application of the aggregation-induced luminochromism of PUH, we doped solid PUH into PMMA in DMF solutions and then prepared PUH-PMMA films by evaporation. The emission spectrum and photographs are shown in Figures 5a,c. The amount of PMMA was fixed at 500

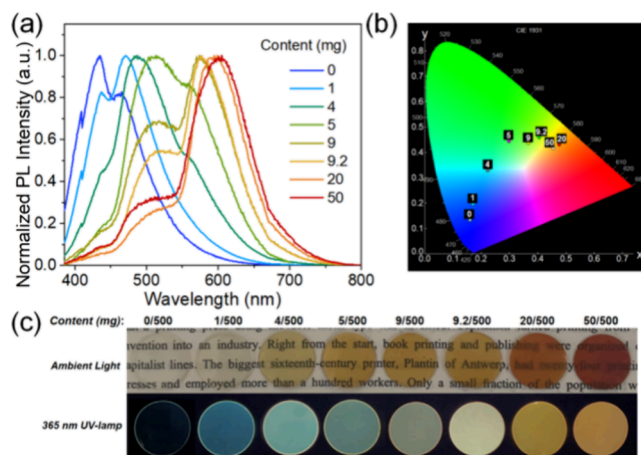


Figure 5. (a) Normalized emission spectra of PUH-PMMA films with different doping ratios. (b) CIE diagram of the multicolor emitting films. (c) Corresponding photographs of the films with different doping ratios.

mg, while the amount of PUH was varied: plastic films with progressive blue to green to orange fluorescence were successfully obtained (Figure 5b). Concentration-dependent color tunability was attributed to the presence of different forms of the PUH molecules in the PMMA matrix. That is, isolated PUH molecules exist in the low-concentration doped film, and then with increased PUH doping, PUH gradually aggregates, thus showing an emission color (Figure 5c) similar to PUH powder (Figure 1a). In addition, based on the complementary color principle, a film should be obtained with white-light emission by regulating the doping ratio. However, when the amount of PUH exceeded 5 mg, the emission of the film was always blue–green–orange, and white light was not observed. The color varied between green and yellow (Figure 5c), and eventually we fixed the amount of PUH at 9.4 mg, which seemed most likely to give white light, and in turn regulated the amount of PMMA. After a series of attempts (Figure S21), a white-light-emitting PUH-PMMA film was obtained at the ratio of 9.4:440 with Commission Internationale de l'éclairage (CIE) coordinates (0.29, 0.34) (Figure S22), which are very close to ideal white light (0.33, 0.33).

In conclusion, the diversity of emission from a single material is important for multifunctional applications. However, multicolor emission depends strongly on the specific molecular conformation and the precise mode of crystal packing. These properties often cannot be controlled or predicted, and the poor processing properties (high brittleness and low flexibility) of crystalline materials greatly limit their practical applications. In this study, we overcame these problems by exploiting aggregation-induced luminochromism, and by changing the aggregation degree of PUH in a PMMA film to obtain multicolor (blue to orange) and white-light-emitting films. Detailed experimental and theoretical calculations show that the final photoluminescent color of the material is closely related to the degrees of polymerization, the strength of the inter/intramolecular interactions, and the final

microaggregation morphology of the material. This work advances the exploration of nonconventional polyurethane chromophores with molecular aggregation and provides new insights for the acquisition of solid state and thin film multicolor luminescent materials for practical applications.

■ ASSOCIATED CONTENT

Data Availability Statement

The data associated with this Article is available in the manuscript and [Supporting Information](#) files.

SI Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acsmacrolett.4c00534>.

Experimental details; Scheme S1; Figures S1–S22; Tables S1–S4; references (PDF)

■ AUTHOR INFORMATION

Corresponding Authors

Yan-Hong Xu – Key Laboratory of Preparation and Applications of Environmental Friendly Materials, Key Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Jilin Normal University, Changchun 130103, China; orcid.org/0000-0002-9930-587X; Email: xuyh198@163.com

Jia-Wei Xu – Ministry-of-Education Key Laboratory of Numerical Simulation of Large-Scale Complex System (NSLSCS) and School of Chemistry and Materials Science, Nanjing Normal University, Nanjing 210023, China; orcid.org/0000-0002-2732-086X; Email: jwxu_njnu@sina.com

Martin R. Bryce – Department of Chemistry, Durham University, Durham DH1 3LE, United Kingdom; orcid.org/0000-0003-2097-7823; Email: m.r.bryce@durham.ac.uk

Authors

Nan Jiang – Key Laboratory of Preparation and Applications of Environmental Friendly Materials, Key Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Jilin Normal University, Changchun 130103, China

Ya-Jie Meng – Ministry-of-Education Key Laboratory of Numerical Simulation of Large-Scale Complex System (NSLSCS) and School of Chemistry and Materials Science, Nanjing Normal University, Nanjing 210023, China

Chang-Yi Zhu – Key Laboratory of Preparation and Applications of Environmental Friendly Materials, Key Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Jilin Normal University, Changchun 130103, China

Ke-Xin Li – Key Laboratory of Preparation and Applications of Environmental Friendly Materials, Key Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Jilin Normal University, Changchun 130103, China

Xin Li – Key Laboratory of Preparation and Applications of Environmental Friendly Materials, Key Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Jilin Normal University, Changchun 130103, China

Complete contact information is available at: <https://pubs.acs.org/doi/10.1021/acsmacrolett.4c00534>

Notes

The authors declare no competing financial interest.

■ ACKNOWLEDGMENTS

The work was funded by the Science and Technology Development Program of Jilin Province (YDZJ202301-ZYTS305; Grant No. 20210101125JC), Industrial Technology Research and Development Program of Jilin Province (Grant No. 2022C039-1); M.R.B. thanks EPSRC Grant EP/L02621X/1 for funding. J.W.X. thanks the Ministry-of-Education Key Laboratory of Numerical Simulation of Large-Scale Complex System (NSLSCS) for their financial and technical support.

■ REFERENCES

- (1) Teran, N. B.; Reynolds, J. R. Discrete Donor-Acceptor Conjugated Systems in Neutral and Oxidized States; Implications towards Molecular Design for High Contrast Electrochromics. *Chem. Mater.* **2017**, *29*, 1290–1301.
- (2) Cameron, J.; Kanibolotsky, A. L.; Skabara, P. J. Lest We Forget-The Importance of Heteroatom Interactions in Heterocyclic Conjugated Systems, from Synthetic Metals to Organic Semiconductors. *Adv. Mater.* **2024**, *36*, 2302259.
- (3) Jiang, N.; Zhu, D. X.; Su, Z. M.; Bryce, M. R. Recent Advances in Oligomers/Polymers with Unconventional Chromophores. *Mater. Chem. Front.* **2021**, *5*, 60–75.
- (4) Han, P. B.; Zhang, G. Q.; Wang, J.; Yao, Y. J.; Qiu, Y. P.; Xu, H.; Qin, A. J.; Tang, B. Z. Highly Emissive Luminogens in Both Solution and Aggregate States. *CCS Chem.* **2023**, *5*, 1686–1696.
- (5) Würthner, F. Aggregation-Induced Emission (AIE): A Historical Perspective. *Angew. Chem., Int. Ed.* **2020**, *59*, 14192–14196.
- (6) Wang, H.; Li, Q.; Alam, P.; Bai, H.; Bhalla, V.; Bryce, M. R.; Cao, M.; Chen, C.; Chen, S.; Chen, X.; Chen, Y.; Chen, Z.; Dang, D.; Ding, D.; Ding, S.; Duo, Y.; Gao, M.; He, W.; He, X.; Hong, X.; Hong, Y.; Hu, J. J.; Hu, R.; Huang, X.; James, T. D.; Jiang, X.; Konishi, G.; Kwok, R. T. K.; Lam, J. W. Y.; Li, C.; Li, H.; Li, K.; Li, N.; Li, W. J.; Li, Y.; Liang, X. J.; Liang, Y.; Liu, B.; Liu, G.; Liu, X.; Lou, X.; Lou, X. Y.; Luo, L.; McGonigal, P. R.; Mao, Z. W.; Niu, G.; Owyong, T. C.; Pucci, A.; Qin, J.; Qin, A.; Qiu, Z.; Rogach, A. L.; Situ, B.; Tanaka, K.; Tang, Y.; Wang, B.; Wang, D.; Wang, J.; Wang, W.; Wang, W. X.; Wang, W. J.; Wang, X.; Wang, Y. F.; Wu, S.; Wu, Y.; Xiong, Y.; Xu, R.; Yan, C.; Yan, S.; Yang, H. B.; Yang, L. L.; Yang, M.; Yang, Y. W.; Yoon, J.; Zang, S. Q.; Zhang, J.; Zhang, P.; Zhang, T.; Zhang, X.; Zhang, X.; Zhao, N.; Zhao, Z.; Zheng, J.; Zheng, L.; Zheng, Z.; Zhu, M. Q.; Zhu, W. H.; Zou, H.; Tang, B. Z. Aggregation-Induced Emission (AIE). *Life and Health. ACS Nano* **2023**, *17*, 14347–14405.
- (7) Chen, X.; He, Z.; Kausar, F.; Chen, G.; Zhang, Y.; Yuan, W. Z. Aggregation-Induced Dual Emission and Unusual Luminescence beyond Excimer Emission of Poly(Ethylene Terephthalate). *Macromolecules* **2018**, *51*, 9035–9042.
- (8) Pucci, A.; Rausa, R.; Ciardelli, F. Aggregation-Induced Luminescence of Polyisobutene Succinic Anhydrides and Imides. *Macromol. Chem. Phys.* **2008**, *209*, 900–906.
- (9) Konopka, M.; Janaszewska, A.; Johnson, K. A. M.; Hedstrand, D.; Tomalia, D. A.; Klajnert-Maculewicz, B. Determination of Non-traditional Intrinsic Fluorescence (NTIF) Emission Sites in 1-(4-carbomethoxypyrrrolidone)-PAMAM Dendrimers using CNDP-based Quenching Studies. *J. Nanopart. Res.* **2018**, *20*, 220.
- (10) Du, L. L.; Jiang, B. L.; Chen, X. H.; Wang, Y. Z.; Zou, L. M.; Liu, Y. L.; Gong, Y. Y.; Wei, C.; Yuan, W. Z. Clustering-Triggered Emission of Cellulose and its Derivatives. *Chin. J. Polym. Sci.* **2019**, *37*, 409–415.
- (11) Han, T.; Deng, H. Q.; Qiu, Z. J.; Zhao, Z.; Zhang, H. K.; Zou, H.; Leung, N. L. C.; Shan, G. G.; Elsegood, M. R. J.; Lam, J. W. Y.; Tang, B. T. Facile Multicomponent Polymerizations toward Unconventional Luminescent Polymers with Readily Openable Small Heterocycles. *J. Am. Chem. Soc.* **2018**, *140*, 5588–5598.

- (12) Studzian, M.; Pulaski, L.; Tomalia, D. A.; Klajnert-Maculewicz, B. Non-Traditional Intrinsic Luminescence (NTIL): Dynamic Quenching Demonstrates the Presence of Two Distinct Fluorophore Types Associated with NTIL Behavior in Pyrrolidone-Terminated PAMAM Dendrimers. *J. Phys. Chem. C* **2019**, *123*, 18007–18016.
- (13) Zhao, Y.; Yan, H.; Xu, L.; He, Y.; Feng, Z.; Feng, W. Nonconventional Aggregation-induced Emission Polysiloxanes: Structures, Characteristics, and Applications. *Aggregate* **2024**, *5*, No. e471.
- (14) Zhang, Z.; Yan, W.; Dang, D.; Zhang, H.; Sun, J. Z.; Tang, B. Z. The Role of Amide (n, π^*) Transitions in Polypeptide Clusteroluminescence. *Cell Rep. Phys. Sci.* **2022**, *3*, 100716–100727.
- (15) Jiang, N.; Zhu, C. Y.; Li, K. X.; Xu, Y. H.; Bryce, M. R. Recent Progress in Nonconventional Luminescent Macromolecules and their Applications. *Macromolecules* **2024**, *57*, 5561–5577.
- (16) Wang, Y.; Bin, X.; Chen, X.; Zheng, S.; Zhang, Y.; Yuan, W. Z. Emission and Emissive Mechanism of Nonaromatic Oxygen Clusters. *Macromol. Rapid Commun.* **2018**, *39*, 1800528–1800534.
- (17) Liao, P.; Huang, J.; Yan, Y.; Tang, B. Z. Clusterization-Triggered Emission (CTE): One for All. *All for One. Mater. Chem. Front.* **2021**, *5*, 6693–6717.
- (18) Zhao, B.; Yang, S.; Yong, X.; Deng, J. Hydrolyzation-Triggered Ultralong Room-Temperature Phosphorescence in Biobased Nonconjugated Polymers. *ACS Appl. Mater. Interfaces* **2021**, *13*, 59320–59328.
- (19) Song, J.; Guo, X.; Chen, H.; Tang, Y.; Han, L. Ascorbic Acid-Caused Quenching Effect of Protein Clusteroluminescence Probe: The Fast Fluorescent Detection of Ascorbic Acid in Vegetables. *Macromolecules* **2023**, *28*, 2162–2175.
- (20) Liu, Y.; Zhu, M.; Sun, J.; Shi, W.; Zhao, Z.; Wei, X.; Huang, X.; Guo, Y.; Liu, Y. A Self-Assembled 3D Penetrating Nanonetwork for High-Performance Intrinsically Stretchable Polymer Light-Emitting Diodes. *Adv. Mater.* **2022**, *34*, 2201844–2201852.
- (21) Liu, B.; Wang, Y. L.; Bai, W.; Xu, J. T.; Xu, Z. K.; Yang, K.; Yang, Y. Z.; Zhang, X. H.; Du, B. Y. Fluorescent Linear CO₂-Derived Poly(Hydroxyurethane) for Cool White LED. *J. Mater. Chem. C* **2017**, *5*, 4892–4898.
- (22) Hu, R.; Qin, A.; Tang, B. Z. AIE Polymers: Synthesis and Applications. *Prog. Polym. Sci.* **2020**, *100*, 101176.
- (23) Ahn, H.; Kim, S. Y.; Kim, O.; Choi, I.; Lee, C. H.; Shim, J. H.; Park, M. J. Blue-Emitting Self-Assembled Polymer Electrolytes for Fast, Sensitive, Label-Free Detection of Cu(II) Ions in Aqueous Media. *ACS Nano* **2013**, *7*, 6162–6169.
- (24) Lai, Y.; Zhu, T.; Geng, T.; Zheng, S.; Yang, T.; Zhao, Z.; Xiao, G.; Zou, B.; Yuan, W. Z. Effective Internal and External Modulation of Nontraditional Intrinsic Luminescence. *Small* **2020**, *16*, 2005035.
- (25) Sun, X. L.; Xue, H.; Gu, X. Y.; Li, D. S.; Xiao, H.; Wan, W. M. Clickable Polymerization-Induced Emission Luminogens Toward Color-Tunable Modification of Non-Traditional Intrinsic Luminescent Polymers. *Macromol. Rapid Commun.* **2024**, *45*, 2400045.
- (26) Xie, Y.; Liu, D.; Zhang, H.; Wang, D.; Zhao, Z.; Tang, B. Z. Clusteroluminescence in Maleimide: From Well-Known Phenomenon to Unknown Mechanism. *ChemRxiv* **2024**, 2573–2293.
- (27) Yang, T.; Zhou, J.; Shan, B.; Li, L.; Zhu, C.; Ma, C.; Gao, H.; Chen, G.; Zhang, K.; Wu, P. Hydrated Hydroxide Complex Dominates the AIE Properties of Nonconjugated Polymeric Luminescent Polymers. *Macromol. Rapid Commun.* **2022**, *43*, 2100720–2100728.
- (28) Luo, J.; Guo, S.; Chen, F.; Jiang, B.; Wei, L.; Gong, Y.; Zhang, B.; Liu, Y.; Wei, C.; Tang, B. Z. Rational Design Strategies for Nonconventional Luminogens with Efficient and Tunable Emission in Dilute Solution. *Chem. Eng. J.* **2023**, *454*, 140469.
- (29) Deng, J.; Jia, H.; Xie, W.; Wu, H.; Li, J.; Wang, H. Nontraditional Organic/Polymers Luminescence with Red-Shifted Fluorescence Emissions. *Macromol. Chem. Phys.* **2022**, *223*, 2100425–2100439.
- (30) Chu, B.; Zhang, H.; Hu, L.; Liu, B.; Zhang, C.; Zhang, X.; Tang, B. Z. Altering Chain Flexibility of Aliphatic Polyesters for Yellow-Green Clusteroluminescence in 38% Quantum Yield. *Angew. Chem., Int. Ed.* **2022**, *134*, No. e202114117.
- (31) Shang, C.; Zhao, Y. X.; Long, J. Y.; Ji, Y.; Wang, H. L. Orange-Red and White-Emitting Nonconventional Luminescent Polymers Containing Cyclic Acid Anhydride and Lactam Groups. *J. Mater. Chem. C* **2020**, *8*, 1017–1024.
- (32) Ji, X.; Tian, W. G.; Jin, K. F.; Diao, H. L.; Huang, X.; Song, G. J.; Zhang, J. Anionic Polymerization of Nonaromatic Maleimide to Achieve Full-Color Nonconventional Luminescence. *Nat. Commun.* **2022**, *13*, 3717.
- (33) Vallan, L.; Bui, A. T.; Jonusauskas, G.; McClenaghan, N. D.; Istif, E.; Mantione, D.; Pavlopoulou, E.; Brochon, C.; Hadziioannou, G.; Cloutet, E. Multicolor Photoluminescence from Nonconjugated Poly(3,4-Dihydropyran) Nanoparticles. *Macromolecules* **2023**, *56*, 4541–4549.
- (34) Niesiobedzka, J.; Datta, J. Challenges and Recent Advances in Bio-Based Isocyanate Production. *Green Chem.* **2023**, *25*, 2482–2504.
- (35) Ju, D. B.; Lee, J. C.; Hwang, S. K.; Cho, C. S.; Kim, H. J. Progress of Polysaccharide-Contained Polyurethanes for Biomedical Applications. *Tissue Eng. Regen. Med.* **2022**, *19*, 891–912.
- (36) Phung Hai, T. A.; Tessman, M.; Neelakantan, N.; Samoylov, A. A.; Ito, Y.; Rajput, B. S.; Pourahmady, N.; Burkart, M. D. Renewable Polyurethanes from Sustainable Biological Precursors. *Biomacromolecules* **2021**, *22*, 1770–1794.
- (37) Wendels, S.; Averous, L. Biobased Polyurethanes for Biomedical Applications. *Bioact. Mater.* **2021**, *6*, 1083–1106.
- (38) Ou, Y.; Wang, X.; He, N.; Wang, X.; Lu, D.; Li, Z.; Luo, F.; Li, J.; Tan, H. A Biocompatible Polyurethane Fluorescent Emulsion with Aggregation-Induced Emission for Targeted Tumor Imaging. *J. Mater. Chem. B* **2023**, *11*, 2266–2275.
- (39) Zhu, X.; Han, K.; Li, C.; Wang, J.; Yuan, J.; Pan, Z.; Pan, M. Tough, Photoluminescent, Self-Healing Waterborne Polyurethane Elastomers Resulting from Synergistic Action of Multiple Dynamic Bonds. *ACS Appl. Mater. Interfaces* **2023**, *15*, 19414–19426.
- (40) Sagara, Y.; Karman, M.; Seki, A.; Pannipara, M.; Tamaoki, N.; Weder, C. Rotaxane-Based Mechanophores Enable Polymers with Mechanically Switchable White Photoluminescence. *ACS Cent. Sci.* **2019**, *5*, 874–881.
- (41) Wang, J.; Yan, R.; Hu, Y.; Du, G.; Liao, G.; Yang, H.; Luo, Y.; Zheng, X.; Chen, Y.; Wang, S.; Li, X. Density-Dependent Emission Colors from a Conformation-Switching Chromophore in Polyurethanes. *Angew. Chem., Int. Ed.* **2022**, *61*, No. e202112290.
- (42) Wang, Z.; Zhang, H. K.; Li, S. Q.; Lei, D. Y.; Tang, B. Z.; Ye, R. Q. Recent Advances in Clusteroluminescence. *Topics Curr. Chem.* **2021**, *379*, 14–36.
- (43) Bauri, K.; Saha, B.; Banerjee, A.; De, P. Recent Advances in the Development and Applications of Nonconventional Luminescent Polymers. *Polym. Chem.* **2020**, *11*, 7293–7315.
- (44) Wu, L.; Holzapfel, M.; Schmiedel, A.; Peng, F.; Moos, M.; Mentzel, P.; Shi, J.; Neubert, T.; Bertermann, R.; Finze, M.; Fox, M. A.; Lambert, C.; Ji, L. Optically Induced Charge-Transfer in Donor-Acceptor-Substituted p- and m-C₂B₁₀H₁₂ Carboranes. *Nat. Commun.* **2024**, *15*, 3005.
- (45) Guo, T.; Lin, Y.; Pan, D.; Zhang, X.; Zhu, W.; Cai, X. M.; Huang, G.; Wang, H.; Xu, D.; Kühn, F. E.; Zhang, B.; Zhang, T. Towards Bioresource-Based Aggregation-Induced Emission Luminescence from Lignin β -O-4 Motifs as Renewable Resources. *Nat. Commun.* **2023**, *14*, 6076–6087.
- (46) Li, J.; Gong, X. One-Step Large-Scale Fabricating Aggregation-Induced Emission Carbon Dots with Strong Solid-State Fluorescence Emission. *Mater. Today Chem.* **2022**, *26*, 101255.
- (47) Zhang, Z.; Xiong, Z.; Chu, B.; Zhang, Z.; Xie, Y.; Wang, L.; Sun, J. Z.; Zhang, H.; Zhang, X.; Tang, B. Z. Manipulation of Clusteroluminescence in Carbonyl-based Aliphatic Polymers. *Aggregate* **2022**, *3*, No. e278.
- (48) Xia, R.; Zhang, Z.; Wu, P.; Wu, Y.; Wang, K.; Li, X.; Ye, M.; Wang, Z. Twisted Vibration of Aza-Azulenene Promotes Ultra-Fast Triplet-Singlet up-Conversion for Extremely Stable Red Electrochromism. *Chem. Eng. J.* **2024**, *479*, 147562.

(49) Yang, T.; Li, Y.; Zhao, Z.; Yuan, W. Z. Clustering-Triggered Phosphorescence of Nonconventional Luminophores. *Sci. China Chem.* **2023**, *66*, 367–387.

(50) Chu, B.; Zhang, H.; Hu, L.; Liu, B.; Zhang, C.; Zhang, X.; Tang, B. Z. Altering Chain Flexibility of Aliphatic Polyesters for Yellow-Green Clusteroluminescence in 38% Quantum Yield. *Angew. Chem., Int. Ed.* **2022**, *61*, No. e202114117.

(51) Bai, L. H.; Yan, H. X.; Guo, L. L.; He, M. M.; Bai, T.; Yang, P. F. Oleic Acid Constructed Supramolecular Hyperbranched Polysiloxane with Enhanced Fluorescence and Excellent Drug Delivery Ability. *Macromol. Chem. Phys.* **2021**, *222*, 2100283.

(52) Wen, B.; Li, A.; Zhao, J.; Guo, H.; Fang, Y.; Lin, Y.; Cheng, H. B. Facile Assembly Strategy for Luminescent Lanthanide Nanoparticles with Antibacterial Activity Using Aggregation-Inducing Emission Polymers. *Macromolecules* **2023**, *56*, 1884–1897.